



## Supplementary Materials for

### **Reducing emissions and air pollution from informal brick kilns: Evidence from Bangladesh**

Nina Brooks *et al.*

Corresponding author: Nina Brooks, [nrbrooks@bu.edu](mailto:nrbrooks@bu.edu)

*Science* **388**, eadr7394 (2025)  
DOI: 10.1126/science.adr7394

#### **The PDF file includes:**

Materials and Methods  
Figs. S1 to S15  
Tables S1 to S60  
References

#### **Other Supplementary Material for this manuscript includes the following:**

MDAR Reproducibility Checklist

# Materials and Methods

## Experimental design

The experimental design was based on our theory of change, which emphasizes working with existing zigzag kiln owners and directly considering their profit motives. We hypothesized this strategy would provide an opportunity to quickly improve the dominant production model, achieve immediate reductions in air pollution and greenhouse gas emissions, and simultaneously increase kiln profits. This was informed by our pilot study (34), critical analysis of past efforts and their effectiveness (15, 24, 32-35, 39-44), studies of brick kilns in Mexico (29-30, 58, 66-67), and research within economics on management interventions (62, 70-74), energy efficiency (1, 4, 12-14, 52, 68-69), and technology adoption (6-11, 38, 59).

The RCT contained three experimental arms: (1) technical, (2) technical+, and (3) control. Kilns assigned to the technical arm received information, intensive training, and technical support to adopt a suite of operational improvements that included improved firing practices, improved brick setting, and increased insulation (see Section below). These operational improvements have the potential to both reduce emissions and energy use, as well as increase kiln profitability, if done correctly, via reduced fuel expenditures and increased revenue from producing more high quality bricks.<sup>1</sup>

The training highlighted the financial benefits of these improvements and included live participation from owners who had adopted them during our pilot study in order to directly address owners' uncertainty regarding economic returns. The training was delivered in the form of initial orientation sessions for owners and their managers, then separate sessions for firing and loading sardar (labor supervisors). These initial sessions were followed by on-site training of sardar and workers in brick loading and firing. Throughout the brick firing season, our team provided technical support to help owners and their workers implement the new practices.

Kilns assigned to the technical+ arm received everything delivered to the technical arm in terms of technical training and support, plus additional information and encouragement that targeted owners to address workers' misaligned incentives. Suggestions included a mix of financial (e.g., bonuses, higher wages, return bonuses) and nonfinancial incentives (e.g., better working conditions, such as meals, housing, and clothing). These examples were directly informed by the experience of other kiln owners successfully operating ZZKs, our own pilot study in Jashore district, and the economics literature (13-14, 62)—including evidence from brick kilns in Nepal (78) and garment factories in Bangladesh (79). The implementation included a preliminary group meeting with all owners assigned to the technical+ arm, in which our team explained the profit-based case for incentivizing workers to adopt the new practices, the importance of workers' properly adhering to the new technical practices and giving them enough time, training, and positive reinforcement to adopt the new practices, and descriptions of several ways to incentivize workers to adhere to the new practices (see the [Incentive Arm Script](#) section below for the script). A handout that described the importance of motivating workers to adopt the new technical practices was left with owners at this initial meeting. Our team conducted two follow-up “nudge” visits to all kilns in the technical+ arm. At the first follow-up nudge visit, they gave owners a poster that presented a few simplified key messages about the importance of incentives as a reminder.

The control arm received no information or training from our team but participated in all data

---

<sup>1</sup>Brick quality is an indicator of both improved efficiency and kiln owner benefits. When bricks are fired in a traditional kiln, the highest quality or properly baked bricks are classified as Class-1 bricks and sold for a higher price than inferior classes. See Section for more details.

collection efforts.

This project was reviewed and approved by Institutional Review Boards (IRBs) at Stanford University (#67263) and ICDDR,B (PR-22052).

## Technical Intervention Details

### Less dense brick stacking with multiple (two or three) zigzag air paths

The existing practice was dense brick setting with single zigzag air path (Fig. S5). Typical packing density<sup>2</sup> and packing fraction<sup>3</sup> was in the range of 1,050-1,150 kg/m<sup>3</sup> and 60%-65%, respectively.

The technical intervention introduced brick stacking that was less dense and formed two or three zigzag air paths. The typical packing density and packing fraction of the setting was in the range of 900-1,000 kg/m<sup>3</sup> and 50%-55%, respectively. A less dense brick setting with two zigzag air paths is shown in Fig. S6. A kiln with less dense brick setting results in better distribution of air in the brick setting, which leads to uniform distribution of heat and temperature and a higher percentage of Class-1 bricks. Better air distribution improves the combustion of coal, and thus reduces the generation of black carbon and small particulates. Also, less dense brick setting results in less pressure loss, and hence requires less energy to drive the fan to create kiln draft.

### Single fireman continuous fuel feeding

The fuel is fed through the feed holes provided at the roof of the kiln by firemen. As per the existing fuel feeding practice, fuel is fed by two or three firemen simultaneously (Fig. S7) at intermittent intervals—i.e., the firemen feed coal simultaneously for an interval of 10-15 minutes, followed by a non-feeding interval of 15-20 minutes. Intermittent feeding by two or three firemen simultaneously results in the accumulation of fuel in the kiln, which does not receive sufficient air for combustion. This results in incomplete combustion, unburnt fuel, and black smoke (excessive particulate matter emissions).

In the improved practice (technical intervention), a single fireman (Fig. S8) feeds fuel continuously for 30 minutes. After 30 minutes he pauses, and his place is taken by his partner fireman. The fuel is fed sequentially in all chambers in the firing zone. This cycle is repeated continuously in the firing zone. In this way, fuel is fed in small quantities continuously, which causes the coal to receive adequate air for combustion. As a result, it burns completely and results in less wasted fuel and less black smoke. It also enables more uniform heat distribution across the kiln cross-section.

### Thicker ash layer on the kiln top

The layer of ash on the top of the brick setting serves as the kiln's temporary roof and provides insulation against heat loss. As per the existing practice, the layer of ash has a thickness of approximately 6 in (Fig. S9). In the improved practice (technical intervention), kilns are encouraged to increase the layer of ash to 9 in or more. Improved insulation due to the thicker ash layer reduces heat loss as well as the in-leakage of cold air into the kiln, helps reduce fuel consumption, and ensures that the top layers of the brick setting will attain a high temperature for baking and thus increase the percentage of Class-1 bricks.

### Closing kiln entry gates with an ash-filled cavity wall

Entry gates are openings in the outer wall of the brick kiln that give workers access to the kiln in order

---

<sup>2</sup>Packing density (kg/m<sup>3</sup>) is the weight of green bricks stacked per m<sup>3</sup> of kiln chamber volume.

<sup>3</sup>Packing fraction of brick setting (in %) can be defined as the volume of bricks stacked in a chamber to the volume of the chamber.

to stack green bricks and remove fired bricks. Once green bricks are stacked, a temporary wall of bricks is made to close the entry gates and seal the kiln. As per the existing practice, the temporary wall to close entry gates is a one-brick (approximately 10 in) thick single wall. As per the improved practice, the wall thickness is increased to 30 in. The wall now consists of two walls: an inner wall of 15-in thickness and an outer wall of 10-in thickness. The two walls are separated by a cavity (5-in thickness) filled with ash. The increased thickness of wicket gate walls and the presence of ash reduces heat loss and air leakage, and thus reduces the amount of coal required to maintain the kiln's temperature. Bricks set close to the entry gate attain a high temperature for baking, which in turn increases the percentage of Class-1 bricks.

### **Use of powdered biomass fuel in the newly inducted chamber in the fuel feeding zone**

In a zigzag kiln, the fire moves around the kiln's firing chamber (a single cycle around the kiln is referred to as completing a circuit). As the fire moves, a new chamber enters the fuel feeding zone every 8-12 hours. The temperature of a newly inducted chamber is initially lower ( $<500^{\circ}\text{C}$ ). In the existing practice, coal is fed into the newly inducted chamber. Since the newly inducted chamber has a low temperature, the coal fed is not able to burn completely; this gives rise to black smoke (particulate matter) and CO emissions. In the improved practice, kilns are encouraged to feed saw dust and other powdery biomass fuels with high volatile matter content and low ignition temperatures into the newly inducted chamber (Fig. S10). These fuels are able to burn completely at a low temperature. Once the newly inducted chamber has attained a temperature higher than  $700^{\circ}\text{C}$ , coal begins to be fed.

## **Sample Selection and Randomization**

We obtained lists of all zigzag kilns operating in Khulna Division from the division and district Brick Manufacturing Owners Associations. The initial sampling frame included 410 zigzag kilns operating in 7 of the 10 districts of Khulna Division. Based on initial conversations with the leadership of each district level Brick Manufacturing Owners Association to gauge their interest in supporting the study and the number of available kilns, we ultimately selected 6 districts for inclusion: Jahsore, Khulna, Jhenaidah, Chuadanga, Kushtia, and Narail. We aimed to enroll 300 kilns in the trial, based on our power calculations and logistical considerations. Figure S11 presents a map of the study districts and kiln locations in Khulna Division.

Field research assistants completed consent procedures and collected baseline data from an initial sample of 328 zigzag kilns from these 6 districts. During the baseline data collection, we learned that many of the initial 410 kilns chose not to operate their kiln that season due to the high price of coal or switching to exclusively using firewood, which rendered them ineligible for the technical intervention (as these were the inclusion criteria). Based on this information, our team consented, enrolled, and collected baseline data from an additional 29 kilns in Jashore District to enroll them in the trial. Thus, we enrolled 357 kilns, which were then randomized into technical ( $n = 119$ ), incentive ( $n = 121$ ), and control ( $n = 117$ ) arms, stratified by district and the prior season's production of class-1 bricks (above or below the median). We ran randomized kilns 1,000 times to create 1,000 different potential allocations and selected the allocation that maximized the sum of p-values across all balance tests (80-82).<sup>4</sup> The overall sample of 357 kilns was balanced on a set of baseline kiln and kiln owner

---

<sup>4</sup>Balance tests were done using the following variables: owner experience, owner education, existence of additional owners, knowledge of pilot intervention in Jashore, interaction with pilot kilns in Jashore, year they changed to ZZK, location, adjacency to water, count of bricks fired in previous year, percent Class 1 bricks in the preceding year, production cost estimates per thousand bricks, number of workers in each kiln job, and average weight of fired bricks.

characteristics, as was the initial sample of 328 kilns and the additional 29 kilns from Jashore.

Figure S12 presents a flowchart of the intervention kilns from baseline data collection to the final analytic sample and Fig S13 is a timeline of all study activities.

## Data collection

We developed four quantitative data collection tools: (1) a baseline/endline questionnaire, (2) an adoption checklist, (3) a kiln performance monitoring tool, and (4) a worker survey. The baseline questionnaire collected information on kiln owner demographics, the GPS location of the kiln, retrospective information on the previous brick firing season (production, costs, revenue), and baseline information about kiln construction and operation.

Initial adoption visits were conducted between January and February 2023, after intervention kilns had been trained. The adoption checklist assessed take-up of the technical intervention components and collected some information on fuel use. We conducted extensive kiln performance monitoring between March and May 2023, after kilns had completed several rounds of brick firing and the firing process had reached an equilibrium in terms of energy use (typically, more coal is used in early rounds of firing, when the ground is cold and wet and green bricks contain more moisture). The performance assessment took approximately 30 hours per kiln and included classifying fired bricks, measuring the quantity of fuel consumed during 24-hours, counting the chambers in which fuel feeding occurred during monitoring, collecting coal samples for measurement of calorific value, and measuring emissions in the flue gas. The kiln performance monitoring tool included the same adoption checklist to assess take-up of the technical intervention components at a second point in time. These visits were not announced in advance to kiln owners. The data collected during the kiln performance monitoring was extremely detailed (see [Kiln Performance Monitoring Protocol](#) and includes objective measures of brick quality, brick quantities, and fuel use. However, we note that the measures were collected at a single point in time and thus are not representative of seasonal averages.

Fieldworkers were unable to complete the performance monitoring assessment in all kilns because kilns had to be operational during these visits and many kilns closed operation early due to the timing of Ramadan. Also, several kilns had been demolished or shut down by the government before the monitoring could be completed; see the subsection that presents the kiln performance monitoring protocol. Our team ultimately completed kiln performance monitoring of 276 kilns, which is the primary analytic sample (Fig. S12). Tables S4-S10 demonstrate that our sample remains balanced after each of these instances of dropout, and attrition due to these reasons is not correlated with the treatment. Data from the kiln performance assessments are used to construct the primary outcomes for this study.

In a subsample of 12 kilns in 4 different districts, a trained team from the Bangladesh University of Engineering and Technology measured suspended particulate matter (SPM) in the chimneys using an isokinetic sampler. Four kilns from each arm were considered in the subsample. Since the stacks lacked any sampling hole and were too thick, these measurements were performed by constructing a temporary chimney that diverted gas from the main chimney and facilitated the necessary particulate matter, moisture content, and velocity measurements. Measurements were performed for a sufficient time to capture the effect of coal feeding and idle time. A simple comparison of SPM by adoption status is presented in Fig. S2, as the small sample precludes any rigorous statistical analysis.

A separate trained team conducted a survey of 1,746 workers across 293 of the study kilns (this sample size did not differ from the final analytic sample size, Fig. S12, because kilns did not have to be operational at the time of the survey and was conducted at a different time). The goal of this

survey was to understand the working conditions at these kilns, as well as worker characteristics and any benefits/incentives workers received. Using questions about working conditions, wages, contracts, and safety considerations, we also calculated the prevalence of labor trafficking according to standardized indicators and the existence of child labor. For each kiln, six individuals were interviewed: five workers spread across four job types (brick molders, brick loaders, brick unloaders, and firemen) and one sardar (work supervisor). Because some job types left early for Ramadan, we allowed for multiple workers of the same job type to be surveyed in order to obtain six individuals per kiln.

The baseline questionnaire was revised and used for endline data collection, which was collected from 328 (out of the original 357) kilns between June and July 2023. The endline survey sample is larger than the kiln performance monitoring sample because this survey did not require that kilns be operational during data collection.

Our primary outcomes are mostly derived from the kiln performance monitoring data. However, certain elements, such as brick prices and fuel spending, were collected only at endline from owners. In cases in which outcomes could be constructed using data reported at endline instead of the kiln performance monitoring data—such as specific fuel consumption, brick production by class, value of production, and fuel spending—we present results using the endline data in Tables [S30](#), [S20](#) and [S28](#). The kiln owner measures reported at endline also differ in their reference period, as owners were asked to recall answers based on the entire season. In contrast, the kiln performance monitoring was collected at a single point in time during the firing season. However, we generally prefer the more objective measures from the kiln performance monitoring data, which are also not subject to recall bias.

## Outcome Measurement Details

In this section we provide detailed explanations of the outcomes assessed in the main manuscript. See Table [S3](#) for summary statistics of each outcome by treatment arm.

### Adoption of the technical intervention

Adoption is defined as taking up both of the recommended brick stacking and firing practices (described in [Technical Intervention Details](#) above) based on objective observations from the evaluation team during the adoption checklist visit and the performance monitoring visit. A kiln must be following both of these recommended practices to be considered an “adopter.”

### Specific Energy Consumption (SEC)

SEC is defined as the thermal energy used in megajoules (MJ) for firing 1 kg of brick (MJ/kg of fired brick); lower SEC is associated with higher energy efficiency. The SEC was calculated based on data collected during kiln performance monitoring over a period of  $24 \pm 2$  hours and is calculated according to the following equation:

$$SEC = \frac{H_{in}}{M_{fbr}} \quad (1)$$

where  $M_{fbr}$  is the mass of fired bricks produced during the monitoring period and  $H_{in}$  is the total thermal energy input to the kiln during the monitoring period, which is calculated as the energy input from external fuel fed into the kiln plus the energy input from internal fuel added to the bricks during soil preparation plus the energy input from organic matter present in the brick soil.



None of the study kilns were used internal fuel during the soil preparation process. The quantity of organic matter in agricultural soil in Bangladesh is small and has declined in recent years (83). Thus, the energy input from organic matter was not considered. Only thermal energy input from the external fuel fed into the kiln during the period of monitoring was considered in our calculations. Therefore,  $H_{in}$  is calculated according to the following equation:

$$H_{in} = \sum_{i=1}^n M_{fe,i} \times CV_{fe,i} \quad (2)$$

where  $M_{fe,i}$  is the mass of external fuel ( $i$ ) fed into the kiln during the monitoring period and  $CV_{fe,i}$  is the gross calorific value of fuel  $i$  in MJ/kg.

Samples of around 1.5 kg fuel of all the fuels being used were collected from the monitored kilns. Of the collected fuel samples, 45 coal samples (Indonesian coal = 35; Indian coal = 3; South African coal = 7) and 21 biomass samples (sawdust = 14; rice husk = 7) were tested for their gross calorific value (GCV) using the ASTM D 5865 standard in a laboratory. The mean GCV value for each type of fuel was used to calculate SEC (Equation 1). Results are shown in Table S11.

### CO<sub>2</sub> Emissions

CO<sub>2</sub> emissions from brick firing were estimated following UNFCCC approved methodology (37). Specifically, CO<sub>2</sub> emissions were calculated as tons of CO<sub>2</sub> entire season brick production according to the following equation:

$$CO_2e = SEC \times M_{fbr} \times CEF \times CC \times Production \quad (3)$$

where SEC is the specific energy consumption of the kiln (Equation 1),  $M_{fbr}$  is the mass of 100,000 fired bricks, CEF is the IPCC default carbon emission factor for the other bituminous coal (25.8 tC/TJ), CC is the carbon to CO<sub>2</sub> conversion factor, which is 44/12 or 3.67, and *Production* is the total number of bricks produced over the entire season (measured in 100,000s), reported by owners at endline. Results are shown in Table S12. We also constructed an alternative measure of CO<sub>2</sub> emissions derived from the carbon fraction in the fuel mix. This measure was calculated as tons of CO<sub>2</sub> emissions produced by each kiln over the entire season brick production according to the following equation:

$$CO_2e = \alpha \times SFC \times MW \times CEF \times CC \times Production \quad (4)$$

where,  $\alpha$  is the mole of CO<sub>2</sub> produced per gram of fuel mix calculated applying the carbon balance method (using data on carbon present in the fuel mix and ratio of CO<sub>2</sub> to CO obtained from the flue gas analysis); SFC is the specific fuel consumption (tons of fuel mix used per 100,000 bricks), explained further below; MW is the molecular weight of CO<sub>2</sub>, which is taken as 44 g/mol; and *Production* is the total number of bricks produced over the entire season, (measured in 100,000s), reported by owners at endline.

The results with both measures are very consistent and presented in Figure S4.

### PM<sub>2.5</sub> Emissions

PM<sub>2.5</sub> emissions from brick firing were estimated using the energy-based emission factor for PM<sub>2.5</sub> emissions. The emission factor for zigzag kilns in Bangladesh (50) was used in these calculations.

$$PM_{2.5} = SEC \times M_{fbr} \times EF_{PM_{2.5}} \times Production \quad (5)$$

where SEC is the specific energy consumption of the kiln (Equation 1),  $M_{fbr}$  is the mass of 100,000 fired bricks,  $EF_{PM_{2.5}}$  is the  $PM_{2.5}$  energy-based emission factor for coal-based zigzag kilns in Bangladesh ( $0.25 \pm 0.18$  g of  $PM_{2.5}$ /MJ of energy input (50)), and *Production* is the total number of bricks produced over the entire season, (measured in 100,000s), reported by owners at endline. Results are shown in Table S13.

### Fuel Spending

Fuel is a kiln owner's most expensive input. By reducing the quantity of fuel used to fire a fixed quantity of bricks (e.g., the specific fuel consumption described below), the technical intervention should reduce the amount of money owners spend on fuel per unit of output. We calculated two measures of fuel spending per quantity of bricks produced. The first is based on the more objective measures of fuel consumption and quantity of bricks that were fired using that coal collected during kiln performance monitoring. Specifically, we calculated the fuel spending per brick using the following equation:

$$FS = \frac{\sum_{i=1}^n Q_i \times P_i}{N} \quad (6)$$

where  $Q_i$  is the quantity of fuel  $i$  consumed during the monitoring (or reported in the endline) and  $P_i$  is the price/ton reported for fuel  $i$ .  $N$  is the total number of bricks fired during monitoring. These results are shown in Table S14. Then, to estimate the total savings on fuel, we applied this per brick measure to the total quantity of bricks produced during this season, which was reported by kiln owners at endline (Table S15. Tables S21 and S22 report the comparable results using only spending on coal.

### Brick Quality

Brick quality is an indicator of both improved efficiency and kiln owner benefits. When bricks are fired in a traditional kiln, the highest quality or properly baked bricks are classified as Class 1 bricks and sold for a higher price than inferior classes. Fired bricks get their strength from ceramic reactions that take place at a high temperature. The temperature depends on the type of soil; for Bangladesh, this is around  $1,000^\circ\text{C}$ . In the kiln, bricks must be raised to this finishing temperature and the temperature should be maintained for a few “soaking” hours to ensure that the entire brick has attained uniformity (84). Class 1 bricks are obtained only when both the finishing temperature and soaking-time conditions are met. If the temperature is lower or sufficient soaking time is not provided, then under-fired (Class 2 and Class 3) bricks are produced. If the temperature or soaking time is exceeded, over-fired bricks are produced (which end up being crushed and sold in cubic feet of broken bricks). The intervention improves the uniformity in kiln temperature in the cross-section, and thus should result in a larger percentage of bricks that achieve the correct finishing temperature and soaking time. In other words, the fraction of bricks that are the highest quality—Class 1—should increase.

During the kiln performance monitoring, the evaluation team organized fired bricks that were unloaded from the kiln that day into classes (Class 1, Class 1.5, Class 2, Class 3, broken bricks) and recorded how many bricks in each class were unloaded. This was used to calculate the percentage of total bricks unloaded during the monitoring period that fell into each category. Results for the % of Class 1 bricks are shown in Table S16 and the entire distribution is shown in the main manuscript in Fig. 3. Also, during the endline survey owners reported the percentage of their total annual production this firing season that fell into each quality class. This measure was used in the supplementary analysis (Table S30 and Fig S3).



## Value of Production

Since kiln owners can time brick sales from multiple production seasons, we do not have direct measures of revenues from each kiln and the endogeneity of sales timing would make such measures hard to interpret, even if available. Instead, we calculate the expected value of production by multiplying the median reported brick prices for each class of brick by the production of each class of brick, then normalizing by the total quantity of bricks produced according to the following equation:

$$VoP = \frac{\sum_{i=1}^5 Q_i \times P_i}{N} \quad (7)$$

where  $Q_i$  is the quantity of brick class  $i$  for  $i \in \{\text{Class 1, Class 1.5, Class 2, Class 3, and broken bricks}\}$  measured during the monitoring (or reported in the endline) and  $P_i$  is the median price reported for brick class  $i$ .  $N$  is the total number of bricks unloaded, counted, and classified during monitoring (or in some specifications,  $N$  is the total production reported by owners in the endline). This “normalized” measure ends up being driven entirely by differences in brick quality. Thus, we report the effect on brick quality in Fig. 3 and the value of production per brick in Table S27 with monitoring data and Table S28 using kiln owner self reports at endline. We also calculate the total value of production for the entire season using the kiln owner reported data on brick quality and production at endline, which is equivalent to  $VoP = \sum_{i=1}^5 Q_i \times P_i$ . These results are reported in Table ???. We can also calculate this by applying the objective brick quality data measured during the kiln performance assessment to the annual production reported at endline, but as the effect sizes for the objective and self-reported brick quality are similar, the total value of production is also similar (Table S29)

## CO/CO<sub>2</sub> ratio

Particulate matter emitted with the flue gases from brick kiln chimneys causes air pollution. There are two main sources of primary particles in flue gas in a brick kiln:

1. Particles from incomplete combustion. This includes soot, tar particles, and char particles.
2. Particles originating from inorganic material in the fuel, primarily ash in the fuel.

In the case of complete combustion, the carbon (C) present in the fuel gets converted into carbon dioxide (CO<sub>2</sub>). If the combustion is not complete, some of the carbon gets converted into carbon monoxide (CO). The carbon monoxide to carbon dioxide (CO/CO<sub>2</sub>) ratio is a good measure of the completeness of combustion (51). The CO/CO<sub>2</sub> ratio is strongly influenced by the kiln’s operation and particularly by the fuel feeding status.

During kiln performance monitoring, measurements of CO and CO<sub>2</sub> were carried out using a flue gas analyzer for a period of around 2 hours per kiln. The analysis was conducted at the point at which flue gases exit the trench and enter the flue duct on their way to the chimney. The fuel feeding status (feeding/non-feeding) was also recorded for the duration of the flue gas analysis. The flue gas analyzer provided data at 5-second intervals, which was first averaged over 1-minute intervals. The ratio of CO/CO<sub>2</sub> was calculated for each time step, and these were averaged over the duration of flue gas monitoring to yield an average CO/CO<sub>2</sub> for the kiln. In addition to the average, the maximum CO/CO<sub>2</sub>, standard deviation, and interquartile range were calculated (note that only the average was prespecified). Supplementary analyses explored the sensitivity of results to dropping abnormal values, as well as estimate specifications on the maximum and variance. See Tables S40-S57.

### Specific Fuel Consumption (SFC)

SFC is defined as the amount of fuel used in tons for firing 100,000 bricks (tons of coal/100,000 bricks); a lower SFC is indicative of more efficient use of coal. This is the metric used by most brick kiln owners to estimate the efficiency of a kiln. SFC was calculated based on data collected during kiln performance monitoring over a period of  $24 \pm 2$  hours and is calculated according to the following equation:

$$SFC = \frac{\sum_{i=1}^n M_{fe,i}}{N_{fbr}} \times 100000 \quad (8)$$

where  $M_{fe,i}$  is the mass of external coal (i) fed into the kiln during the period of monitoring and  $N_{fbr}$  is the number of bricks fired during the period of monitoring. Additionally, specific coal consumption is calculated as the equivalent measure, based only on coal used (rather than all fuels used). Since coal is used in the largest quantities, specific fuel consumption and specific coal consumption are similar (Table S19).

### Annual Production

The total quantity of bricks (in 100,000s) produced during this firing season (2022-2023) was collected from owners during the endline survey. This measure, which was not prespecified, was used to assess potential rebound effects and results are shown in Table S24.

### Circuits Completed

In a zigzag kiln, the fire moves around the kiln's firing chamber (a single cycle around the kiln is referred to as completing a circuit). The total number of firing circuits completed was collected from owners during the endline survey. On average, kilns in our sample completed 5 firing circuits during the 2022-2023 season. This measure, which was not prespecified, was used to assess potential rebound effects and results are shown in Table S25.

### Worker Incentives and Work Conditions

To analyze the impact of the worker incentive arm and the specific messaging delivered, we examined outcomes related to the provision of any benefits, provision of any benefits to the firing or loading teams, and the presence of several aspects of better working conditions: whether the kiln provides meals, cooking fuel, or a shed for resting. These are shown in Fig. 5 (in the main paper).

## Statistical Methods

To estimate the treatment effects of the intervention, we regressed outcomes on indicator variables for treatment status.

$$Y_i = \beta_0 + \beta_1 T_i + \beta_2 I_i + \gamma_s + \epsilon_i \quad (9)$$

where  $Y_i$  is an outcome of interest for kiln  $i$ ,  $T_i$  is a binary indicator for assignment to the technical only arm, and  $I_i$  is a binary indicator for assignment to the incentive arm. The coefficients on each treatment indicator,  $\beta_1$  and  $\beta_2$ , respectively, capture the “intention-to-treat” (ITT) effect of assignment to the treatment arms on each of the outcomes relative to the control arm and  $\delta_s$  is an indicator for the strata. We will also estimate a version of Equation 9 in which we bundle treatment into a single treatment indicator that captures the ITT effect of assignment to either treatment arm (Equation 10).

Heteroskedasticity-robust standard errors are calculated for all specifications.

$$Y_i = \delta_0 + \delta_1 G_i + \gamma_s + \epsilon_i \quad (10)$$

Because we did not expect all 200 kilns assigned to the treatment arms will adopt the technical intervention (where adoption is defined as taking up both of the recommended brick stacking and firing practices), we also estimated instrumental variable (IV) specifications. This allows us to quantify the impact of the technical intervention among the kilns that *actually* took up the recommended practices. Because non-adoption and noncompliance are not random but likely the result of systematic differences between kiln owners that are likely correlated with the outcomes, our second approach is to use the random assignment as an instrument for adoption in an instrumental variables analysis that measures the local average treatment effect (LATE) among the kilns that took up the intervention (e.g., the compliers) (75,85).

In the absence of defiers (so that only compliers, never-takers and always-takers are present in the language of Imbens and Angrist (75), the ToT parameter is equal to a weighted average of the treatment effect among compliers and the treatment effect among always-takers. If we rule out always-takers, then the ToT parameter is equal to the average treatment effect (ATE) among compliers and is consistently estimable using IV. In the presence of always takers (which is likely the case in our setting since 20% of control kilns adopted the intervention) the ToT is no longer identified, although the ATE among compliers continues to be identified (and is consistently estimable using IV). For this reason we refer to our estimand at the IV effect (or equivalently the LATE).

To estimate the IV, we used the following two-stage least squares (2SLS) approach:

$$A_i = \theta_0 + \theta_1 G_i + \gamma_s + \epsilon_i \quad (11)$$

$$Y_i = \gamma_0 + \gamma_1 A_i + \gamma_s + u_i \quad (12)$$

Equation 11 is the first stage in which adoption ( $A_i$ ) of the two most critical intervention components (double or triple zigzag brick setting and single fireman continuous coal feeding) is predicted with the randomly assigned treatment (using a bundled treatment indicator,  $G_i$ ). Then, in the second stage, Equation 12, we regress an outcome on the instrumented adoption and  $\gamma_1$  captures the IV effect of adopting the intervention on the outcome. Heteroskedasticity-robust standard errors are calculated for all specifications.

To provide context for interpreting the magnitudes of the regression coefficients, we also present the results as a percentage change relative to the control mean for both the ITT and IV specifications. For the IV, the control mean does not account for the non-compliance (e.g., adoption by control kilns) and may represent an underestimate in terms of the percentage change. However, when we use the Imbens and Rubin method (76) to recover  $\mathbb{E}(Y_0|C)$ , the results are similar.

We explored heterogeneity in the primary outcomes across dimensions such as kiln owner years of experience in the brick industry, kiln owner education, whether the kiln owner is involved in other businesses, and kiln location. Our preregistered analysis plan specified that we would examine heterogeneity in the primary outcomes by baseline kiln characteristics, including owner's experience,

owner's education, location on highland, and whether the kiln is a joint proprietorship. For brevity, we present these results in Table [S32](#) and find no significant differences in the treatment effects by these characteristics at the standard 5% level. Although our pre-analysis plan includes a correction for multiple hypothesis testing for the heterogeneous models, we do not make this correction given that the uncorrected interaction terms are statistically insignificant.

Our trial and analysis was preregistered with [AEA](#) (#AEARCTR-0010127) and the [ISRCTN](#) (#ISRCTN15354089). Any specifications that deviate from this plan are stated.

## Incentive Arm Script

Kilns that were randomized into the technical+incentive arm received a detailed information session along with the hands-on training provided with the technical intervention. In these information sessions, our team described how our pilot work increased brick quality while decreasing fuel use, and that achieving these benefits depends on the ability to align worker incentives with the new production method, providing evidence that pilot firms that increased worker pay experienced greater benefits. The complete script is as follows:

[Begin Script]

I'm here to talk to you about how you can get more profit in this year's brick production. We are glad you are working with us to implement the new practices, but their success depends on every worker on your kiln. Our team is here to help with technical training and assistance to make sure your workers have the proper skills to implement everything correctly. **If everyone on your kiln works together and follows the instructions, you will use less coal and increase your production of Class-1 bricks. As a result, these new practices will increase your profit and your kiln will be more successful.**

*How do we know this?*

Our team worked with similar brick kilns in Jashore, and a 14% increase in the percentage of Class-1 bricks and a 20% reduction in coal spending per brick in kilns that successfully followed the recommended practices of single fireman continuous coal feeding and double zigzag brick setting owners saw, compared to kilns using traditional methods.

What's more interesting is that the owners from Jashore that provided more incentives and benefits to their workers had even higher Class-1 bricks (on average, 5 percentage points higher) and lower coal spending (on average, 0.42 Taka less per brick) compared to kilns that did not offer additional incentives.

*How can you reap the same benefits?*

The workers on your kiln are crucial for the success of this new practice. They have to learn the new practices and at first they may not want to change from the old way of doing things. If your workers invest the time to master the new skills it will lead to huge benefits for you. Now, you can imagine when they are learning the new practices they might move more slowly which might reduce their pay. If they do not feel motivated to adopt the new practices, they may take shortcuts or not learn it properly unless you find a way to include them in the success you will have from these new practices.

You may also consider the time and effort you are putting in to having your workers trained on these new practices. They are learning many new skills which will make your kiln successful. You will benefit if you can use the same workers next season, because they will already have the experience and training on these new practices. If you can encourage workers to return, it will be very beneficial to your kiln operation and production.

Because all workers on your kiln must be successfully adopt these practices and work together to increase your production and profit, we recommend any incentives or extra bonus be offered to all workers.

We have some suggestions that other kiln owners like you have used and found to be successful at increasing their kiln performance, getting better performance from workers, and commitments from workers to return to the same kiln:

1. Providing some extra monetary incentives to the workers to motivate them to follow this new practice properly. This will be easily covered by your increased profit /production soon. Because all workers on your kiln must be successfully adopt these practices and work together to increase your production and profit, we recommend incentives be offered to all workers. Successful kiln owners have used incentives differently for different categories of workers, for example, firing workers are given lump sum bonuses after a circuit, whereas unloaders and loaders are given bonuses in terms of 1000 bricks.
2. There are easy improvements you can make for your workers to make them happier and healthier to motivate them be more productive. If your kiln gets a reputation for being a good place to work, where workers are well-taken care of, your workers are more likely to return next season and more workers will want to work for you.

*How can you make incentives and benefits work for you?*

When offering these incentives, it is very important that the workers themselves receive the benefit. Otherwise, they will not be motivated to adopt the new practices, trust will be lost, and your kiln will not benefit. You may encourage the sardars to provide these benefits to workers so that the workers will adopt the practices. Some owners provide benefits directly to the workers to make sure they receive them. A common practice of successful owners is to announce a particular day and time and request all workers and sardars be present, then owners hand over bonuses/bakhshish by themselves. This practice is successful because everyone will give credit to the owner for the extra benefits.

It is also important that you provide the incentives and benefits in a timely manner and early in the season. If it is too late, the workers may not be encouraged to follow the new practices and you will not see the benefit in time.

[Ask: Any questions on what we have talked about so far?]

*What are examples of monetary incentives and good working conditions that you can provide?*

We have put together a list of suggestions from successful kiln owners for you to think about:

1. You may offer a 'Bakhshish' from the higher earnings that you will get by adopting our suggested practices. For example, you can offer a Bakhshish to your workers such as 5-10%, which can be shared across all the workers. One successful kiln owner has provided 10000 Tk to the loading Sardar for adopting the new system and he committed to providing it subsequently in the next rounds of brick stacking. If you inform them at the beginning of each circuit about the

Bakhshish and the importance of following the new practices to achieve a higher amount, it will motivate their performance during the circuit.

2. You may offer a bonus (onudan) to the workers if your kiln achieves a certain level of class-1 bricks in each circuit. We have provided a guideline for the bonuses depending on the share of class-1 bricks. For example, you may offer BDT 5000 if your kiln achieves 80-85% class-1 bricks in a cycle, BDT 6000 if you achieve 85-90% class-1 bricks, and BDT 7000 if you achieve >90% class-1 bricks. You can adjust the schedule given your kiln's performance. We suggest you inform workers at the beginning of the circuit about the bonus to motivate their performance and deliver the payment at the end of the circuit once the brick quality has been assessed.
3. You can also provide 'Bakhshish' of extra Taka 50 per 1000 bricks if your kiln achieves 80-85% class-1 bricks, extra Taka 100 per 1000 bricks if your kiln achieves 85-90% class-1 bricks, or extra Taka 150 per 1000 bricks if your kiln achieves >90% class-1 bricks.
4. Some of the recommended practices will require more time involvement for the workers. For example, in the new method, workers need to increase the ash layers by 9-12 inches from the previous setting. In the new method, fire travels faster and more loading of bricks is necessary to keep up the fire travel in a circuit. In both cases, you can consider increasing the wages of the workers by Taka 10-50 per 1000 bricks to account for the changes.
5. You may offer a return bonus if workers return to your kiln the next season. Inform them of the bonus offer before the end of the current season, so that it can encourage them to return the next year. For example, some kiln owners have offered a bonus equal to 20% of the workers current wages if they return the following season, which will be paid only after they return.
6. You might see that some of your workers want to leave for other working options during the firing season, especially on agricultural fields. To prevent workers who have been trained on these new and improved practices from leaving in the middle of an active season, kiln owners have provided instant bonuses in cash. By making your kiln a more desirable and better paying place to work, the workers will not want to leave for other options.
7. Many kiln owners have successfully retained a higher presence of workers by offering 'attendance bonuses.' You can offer some bonuses for the top 5 workers who are most regular in your kilns to motivate all the workers to avoid shirking.

## Power Calculations

Based on our pilot results, we have estimated effect sizes for the "intention-to-treat" (ITT) effect of each experimental arm, as well as an estimate of adopting (IV) that accounts for imperfect compliance with the intervention (both from kilns assigned to the treatment arm that did not take-up the intervention practices and from control kilns that sought to learn the intervention practices) by using random assignment to both arms as an instrument for adoption. These results for each of the three outcomes are summarized in Table S58 below. We first calculate the minimum detectable effect size (MDES) assuming both arms have equal effect sizes, a significance level of 0.05 and power of 0.9. Then, because there is suggestive evidence from our pilot that the incentive arm encouraged better adherence to the improved operating practices and resulted in better outcomes, we also calculate our



statistical power for detecting differences between the incentive and technical arms.

Fig. S14 presents the minimum detectable effect sizes against the sample size per treatment arm for the percent of class-1 bricks produced, CO/CO<sub>2</sub> ratio, and specific energy consumption. The estimated ITT effects for each arm from the pilot study are indicated in red (incentive arm) and blue (technical arm). These scenarios indicate that with a sample size of 100 kilns per experimental arm (300 total kilns), we are powered for all three outcomes with 90% power in most cases. For class-1 bricks the incentive arm performed much better, producing 7.12 percentage points more class-1 bricks than the control group and we would be powered to detect an effect size of this magnitude with only 25 kilns per arm. The effect size for the technical arm was much smaller (2.1 percentage points higher than the control group) and with 100 kilns per arm, we would not be powered to detect such a small difference. However, 2.1 percentage points is an extremely conservative estimate for a potential effect size. The minimum detectable effect size for 100 kilns per arm at 90% power is 3.56 percentage points. This is half the magnitude of the incentive arm and still relatively conservative, particularly when considering the TOT estimate of 9.22 percentage points among adopters.

For the CO/CO<sub>2</sub> ratio, with 100 kilns per arm, we almost are powered for the more conservative ITT effect attained by the incentive arm but more than sufficiently powered to detect the larger effect size attained by the technical arm. With 100 kilns per arm at 90% power, we are powered to detect an effect size of -0.0064 in the CO/CO<sub>2</sub> ratio, while we would need only 65 kilns per arm to detect an effect as large as -0.008, which is what the technical arm attained in the pilot. Somewhat surprisingly, the measured CO/CO<sub>2</sub> ratio in the pilot was lower in the technical arm than in the incentive arm. This may simply reflect that the CO/CO<sub>2</sub> ratio is a cross-sectional measure that we captured based on data from a few hours in each kiln and so may not accurately reflect the performance over the whole season. Indeed, the first CO/CO<sub>2</sub> ratio was measured before the incentive arm was even rolled out. Nevertheless, the calculations suggest that we will have sufficient power to be able to detect changes in CO/CO<sub>2</sub> ratio with the interventions.

Similar to the percent of Class-1 bricks, our pilot results suggest kilns assigned to the incentive arm had a much lower specific energy consumption (SEC). While we will not be powered to detect effect sizes as small as what the pilot found in the technical arm, we are powered to detect effect sizes smaller than what the technical arm attained. With 100 kilns per arm at 90% power, we are powered to detect an effect size of -0.065 in SEC, while we would need 70 kilns per arm to detect an effect as large as -0.083, which is the ITT effect for the incentive arm compared to the control group. We summarize the minimum detectable effect sizes for a study with 100 kilns per arm with power of 80% and 90% in Table S59.

It is also of interest to assess the power for detecting differences between the two arms. Although we were not powered in the pilot to statistically detect differences in the exploratory outcomes between the technical and incentive arms, our pilot provides suggestive evidence that kilns assigned to the incentive arm performed better than the technical-only arm, although statistically, we cannot rule out equivalent effects. Using these effect sizes and assuming 100 kilns per arm, we estimated the power we can expect to attain for each outcome, which is presented in Table S59. Given the small differences between the two arms, we are underpowered except for the percent of class-1 bricks, where we estimate having 80% power to detect a difference of 5 percentage points.

## Kiln Performance Monitoring Protocol

Kiln performance monitoring was carried out in 276 kilns to collect outcomes for the trial (see Fig. S13 for the field activities timeline). Each monitoring visit was spread over 3 days (from 2 pm on Day 1 to around 10 am on Day 3). The monitoring teams consisted of one engineer and one research assistant. They were further assisted by one or two workers/helpers.

### Timing of Monitoring

The performance of a brick kiln varies throughout a brick-firing season. Circuit-wise performance data were collected from a zigzag kiln located near Kolkata in India.<sup>5</sup> Data on the time taken to complete one kiln circuit and the SFC for a circuit are plotted in Fig. S15.

The brick-firing season can be divided into three phases:

1. Initial Phase (November to Mid-February): This is the winter period, during which the kiln structure and ground are wet from the water absorbed during the rainy season and green bricks loaded in the kiln have higher moisture content. As a result, the SFC and the time required to complete one circuit are higher.
2. Mid-Phase (Mid-February to end April): This is the spring and summer period. After a few circuits have been completed, the kiln structure and ground dry up; due to the dry weather, green bricks loaded in the kiln have lower moisture. The kiln achieves a steady state, and SFC is lowest.
3. End Phase (May-June): By this time, pre-monsoon rains are common and SFC again rises.

Based on this information, kiln performance monitoring was carried out during the mid-phase of the kiln operation when the kiln is operating at steady state. All kilns were monitored between February 20, 2023, and May 11, 2023.

To ensure that kiln performance was monitored when kiln operation was not disturbed and was representative of normal kiln operation, the following criteria were applied:

- The weather at the time of monitoring was dry.
- The kiln was not experiencing any shortage of labor to operate the kiln.
- The kiln had an adequate quantity of coal and green bricks for normal operation.
- The fire was located in the straight portion (which has a zigzag brick setting) of the kiln circuit.

Each monitoring team was equipped with following equipment and materials:

1. A platform balance scale (50-100 kg, with LC of 10 gm)
2. A container for fuel measurement
3. Flue gas analyzer and equipment
4. Fully charged and cleaned flue gas analyzer

---


<sup>5</sup>Personal communication between Greentech and Ashok Tewari, Owner, LMB Brick Kiln, Howrah, Kolkata.

5. Flue gas analyzer probe packed in PVC pipe case
6. Flue gas charger
7. 2 ft steel tube for placement of the probe
8. Napkin/cloth/tissues for cleaning the analyzer
9. Cloth and umbrella for protecting the flue gas analyzer
10. KANE Live program downloaded and installed on the mobile device/tablet.
11. Steel measuring tape (5 m)
12. Steel scale (12 in)
13. Tarpaulin sheets to cover an area of 10 m x 10 m
14. Zip polythene bags (2 kg size), labels, permanent marker, cello tape for sealing fuel sample bags.
15. Computer tablet for data recording and entry in ODK
16. Hardback notebook and pens
17. Placards for marking unloaded brick stacks
18. Bicycle pump for cleaning the probe
19. Set of multiplugs for electrical connections
20. Screwdrivers/tester.


The complete schedule of activities during the monitoring period is reported in Table [S60](#)

## Supplementary Figures


**Fig. S1.** Year 2 Adoption by Treatment Arm. This figure presents the raw means of adopting double/triple zigzag brick stacking and single fireman continuous feeding by treatment arm across two firing seasons. Results from the RCT firing season (2022-2023) are shown in grey and results from a follow-up conducted during the subsequent year's firing season (2023-2024) are shown in orange.

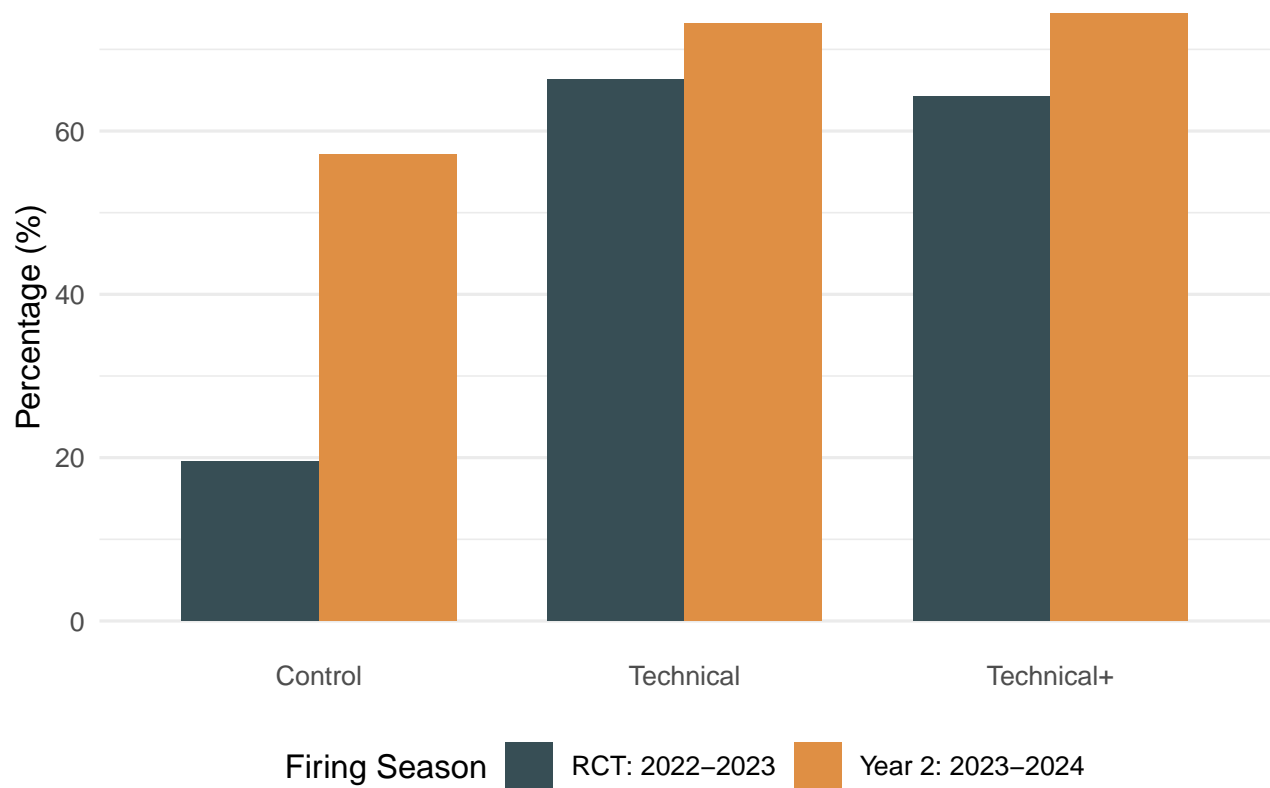

**Fig. S2.** Mean Suspended Particulate Matter by Adoption. Suspended particulate matter was measured in a subsample of 12 kilns (8 adopters, 4 non-adopters, where adoption is defined as adopting both the improved stacking and improved coal feeding practices).

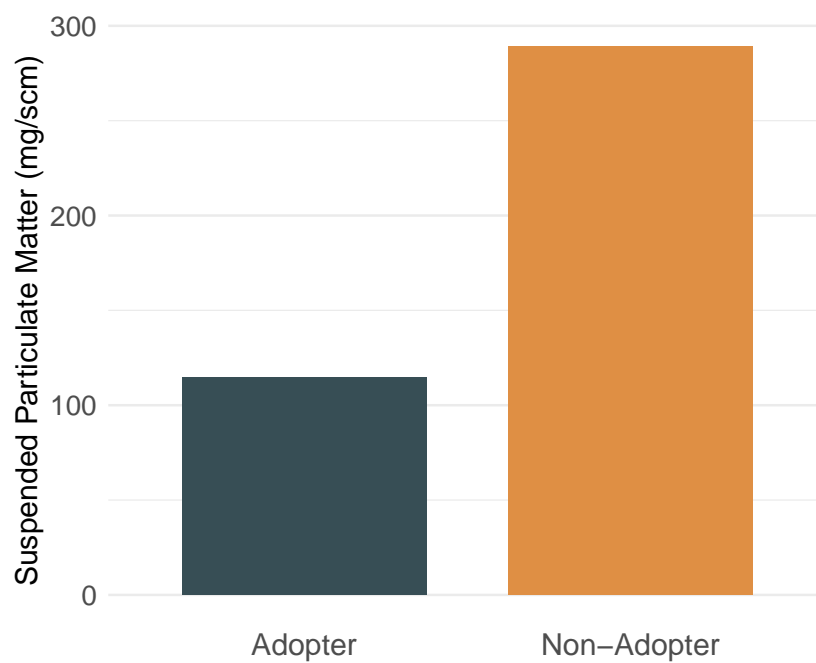


**Fig. S3.** Intervention Impact on Distribution of Brick Quality (Endline). This figure presents regression results for the intention-to-treat (ITT) and instrumental variable (IV) specifications for each classification of brick quality as a percentage of total production, using data reported by kiln owners at endline. The ITT specification, shown on the left in dark gray, bundles both treatment arms. The IV specification, shown on the right in orange, uses random assignment to either treatment arm as an instrument for adopting the technical intervention, and can be interpreted as the effect of adopting the intervention among compliers on a given outcome. Both specifications include randomization strata fixed effects and estimated heteroskedasticity-robust standard errors. In each panel, coefficients are denoted by dots and vertical bars represent 95% confidence intervals around the regression coefficient.

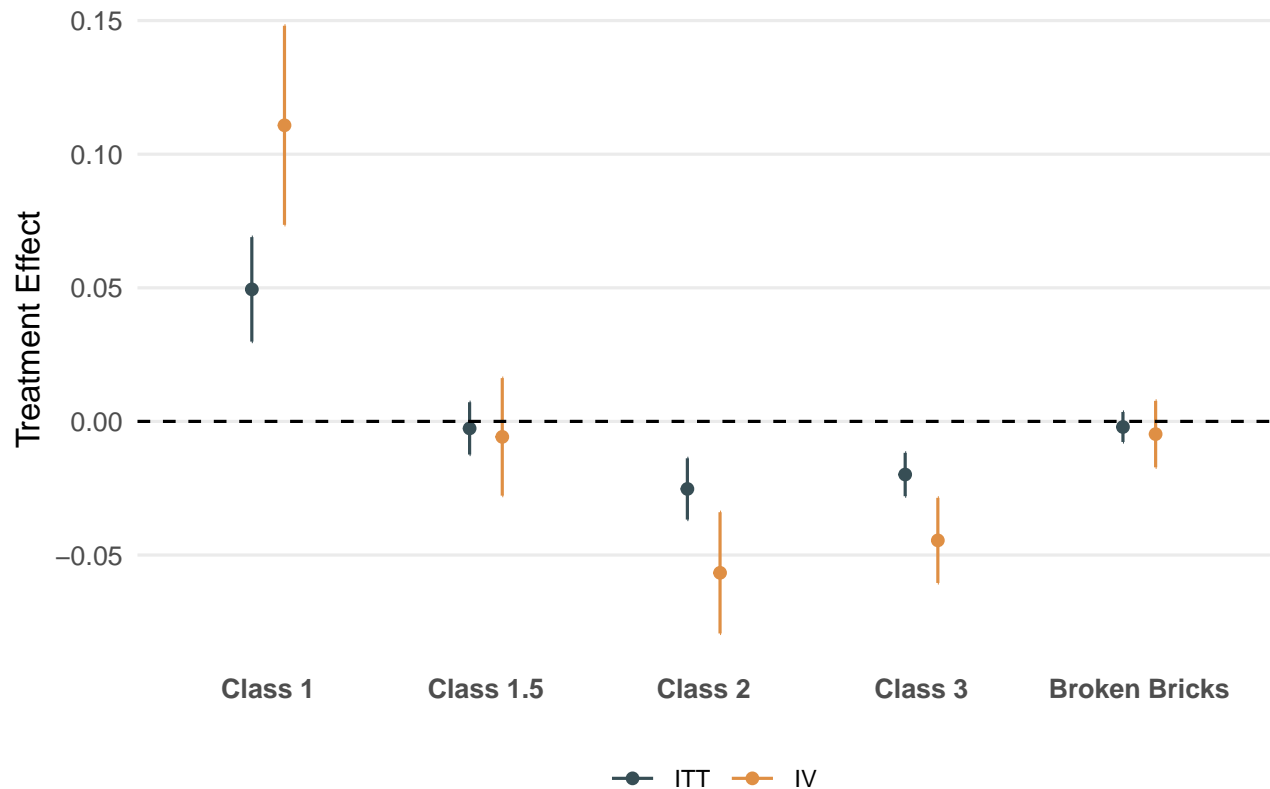





**Fig. S4.** Alternative Approach to Estimating CO<sub>2</sub> Emissions. This figure compares the ITT and IV results of the primary approach to estimating CO<sub>2</sub> emissions, in which the measure is derived from specific energy consumption to an alternative approach that uses the carbon fraction in the fuel mixture with the flue gas data, as described in the Materials and Methods.

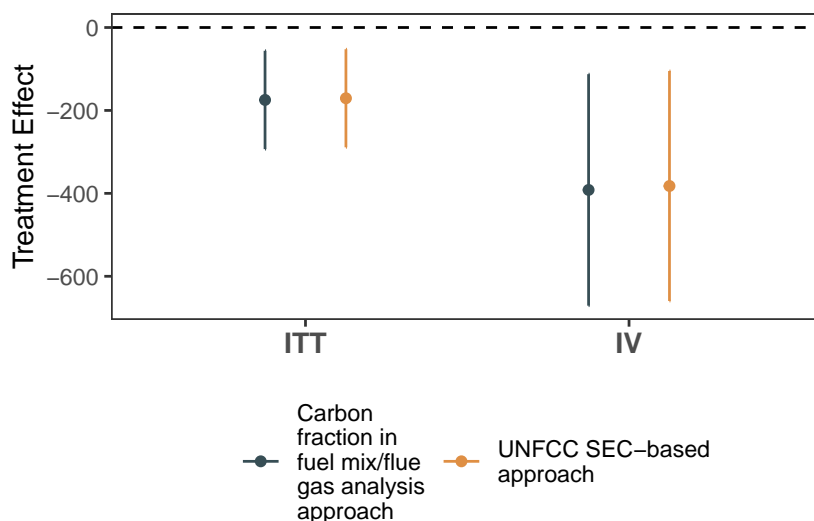

**Fig. S5.** Dense zigzag brick stacking with single zigzag path. This picture shows the standard dense brick setting practice (left) and the resulting airflow in a single zigzag path. See [Technical Intervention Details](#) for details.

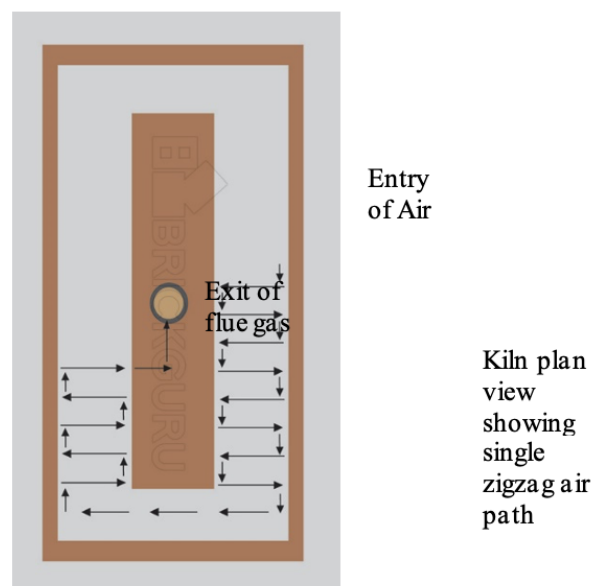

**Fig. S6.** Less Dense zigzag brick stacking with double/triple zigzag path. This picture shows the less dense brick setting practice recommended by the technical intervention (left) and the resulting airflow in a two zigzag paths. See [Technical Intervention Details](#) for details.

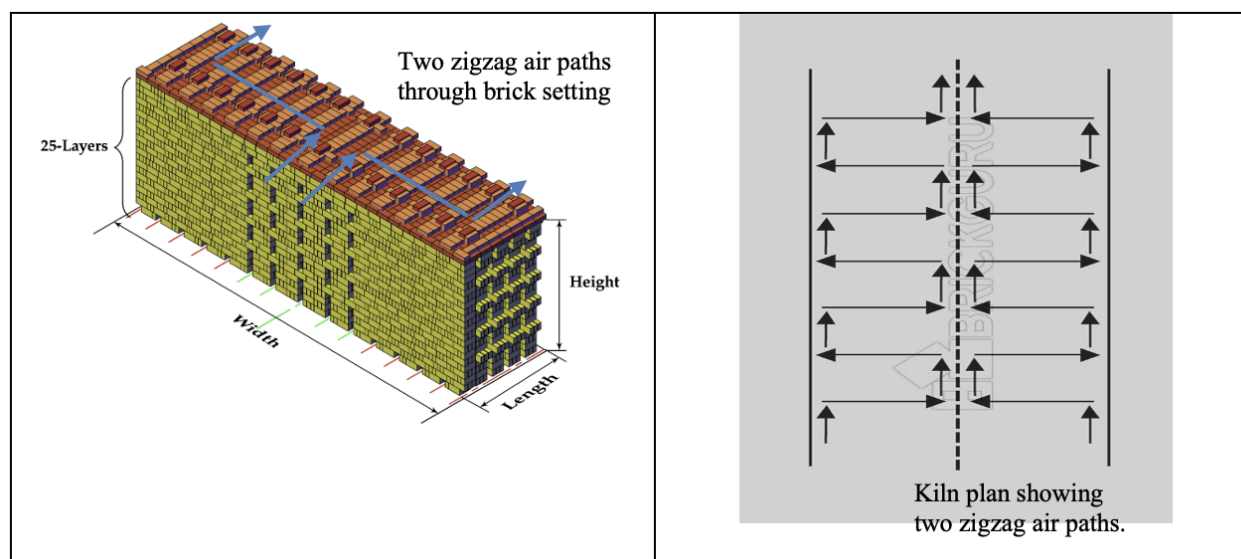

**Fig. S7.** Intermittent fuel feeding by 2 or 3 firemen simultaneously. This picture shows the standard practice of 2-3 firemen feeding coal simultaneously into the kiln. See [Technical Intervention Details](#) for details.




**Fig. S8.** Continuous fuel feeding by a single fireman. This picture shows the practice recommended by the technical intervention of a single fireman feeding coal. See [Technical Intervention Details](#) for details.






**Fig. S9.** Ash layer on top of the brick setting. This picture shows the ash layer used for insulation on top of the kiln and indicates the intervention recommended practice of an ash layer of at least 9 inches. See [Technical Intervention Details](#) for details.

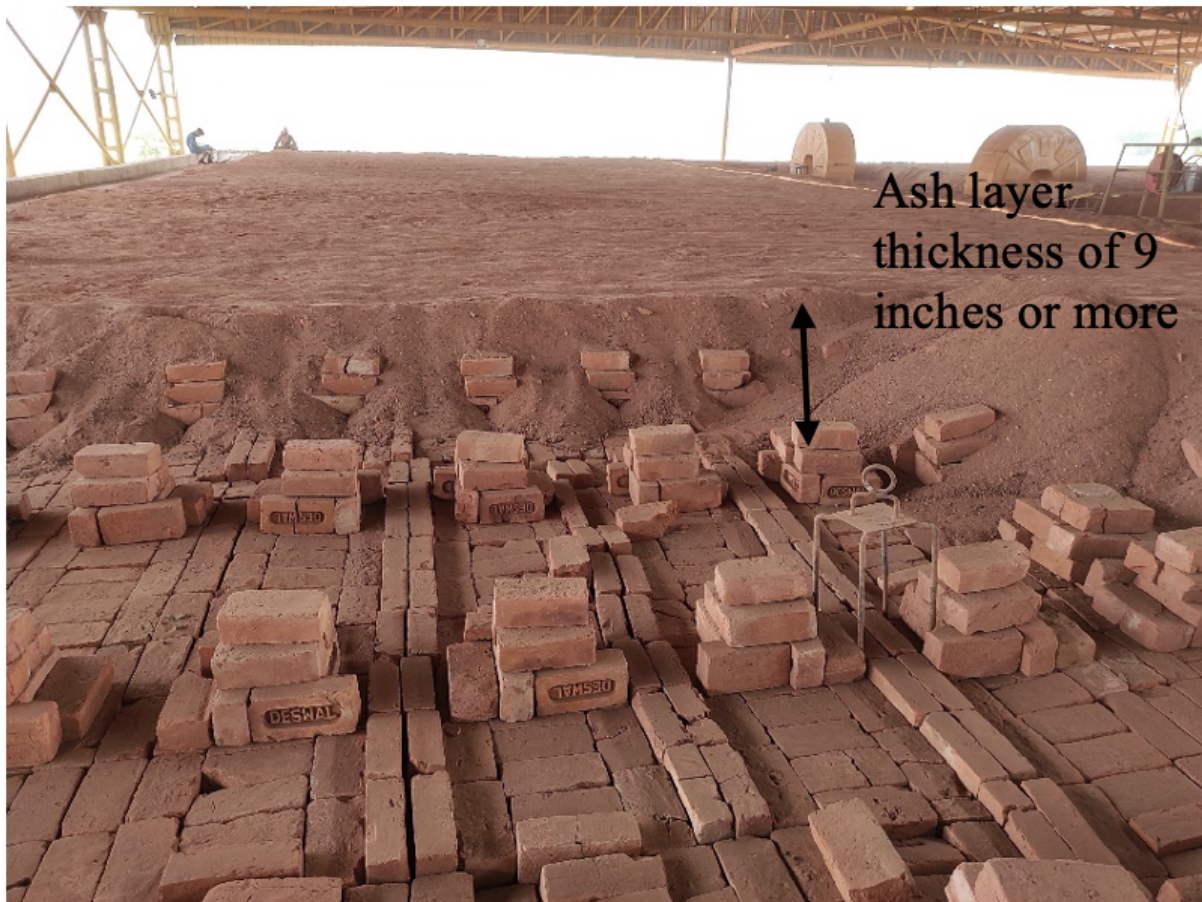

**Fig. S10.** Sawdust for feeding in newly inducted chambers in the fuel feeding zone. This picture depicts the practice of using sawdust in the front chambers of firing, as recommended by the technical intervention. See [Technical Intervention Details](#) for details.




**Fig. S11.** Map of Study Kilns, Khulna Division, Bangladesh. The study was conducted in the 6 districts indicated on the map: Jhore, Khulna, Jhenaidah, Chuadanga, Kushtia, and Narail. Kilns assigned to control arm are shown in red, the technical arm in green, and the technical+incentive arm in blue.

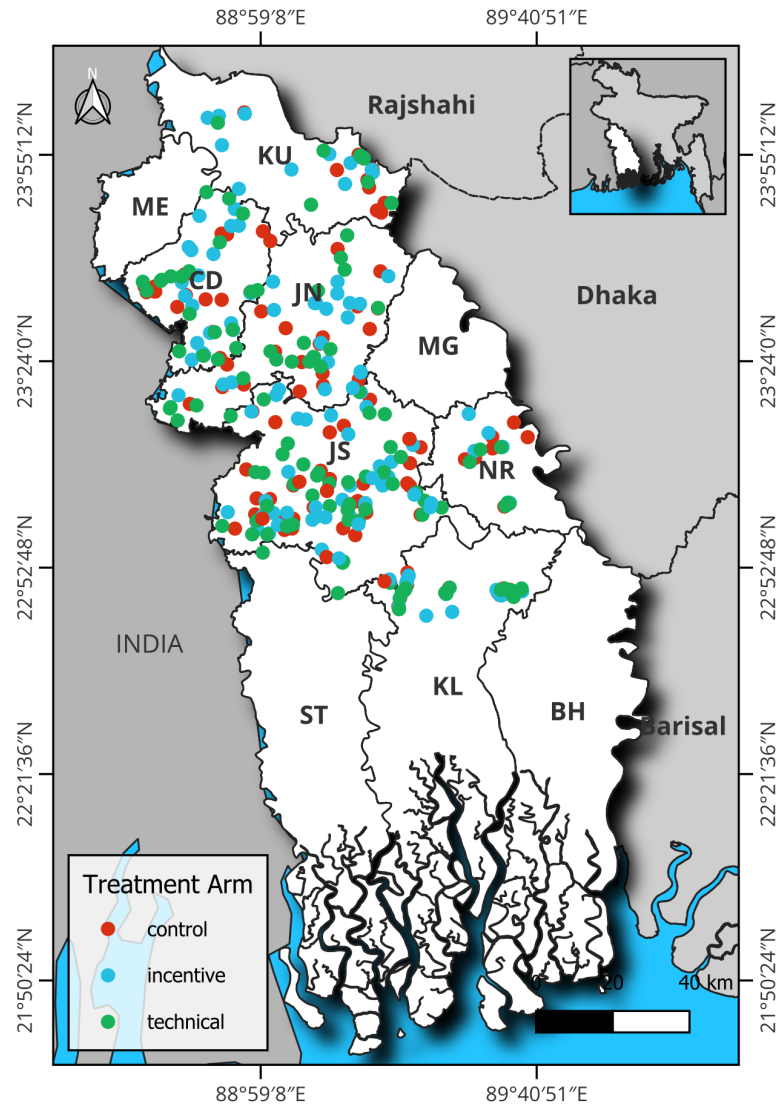





**Fig. S12.** Flowchart of sample size from baseline data to final analytic sample. Flowchart of sample size from baseline data collection to final analytic sample. Reasons for dropout at each stage, as well as number of kilns that dropped out for each reason, are reported. See [Materials and Methods](#) for details.

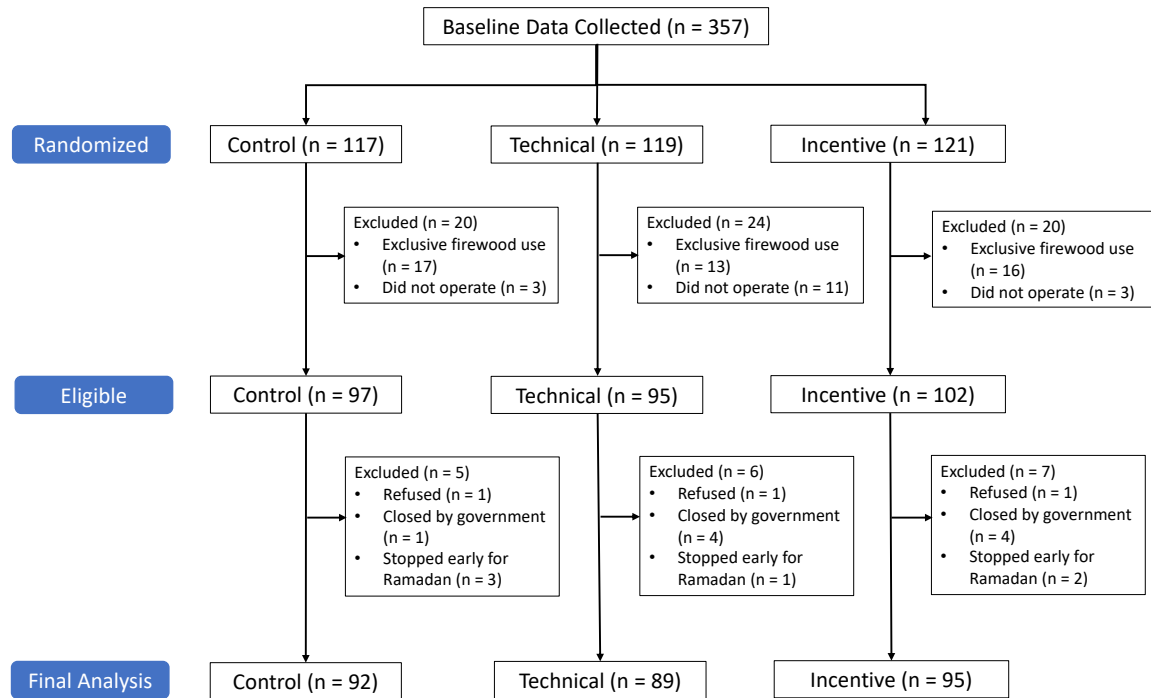


**Fig. S13.** Timeline of fieldwork activities. This figure presents the timeline of field activities and data collection during the 2022-2023 brick firing season. See [Materials and Methods](#) for details.

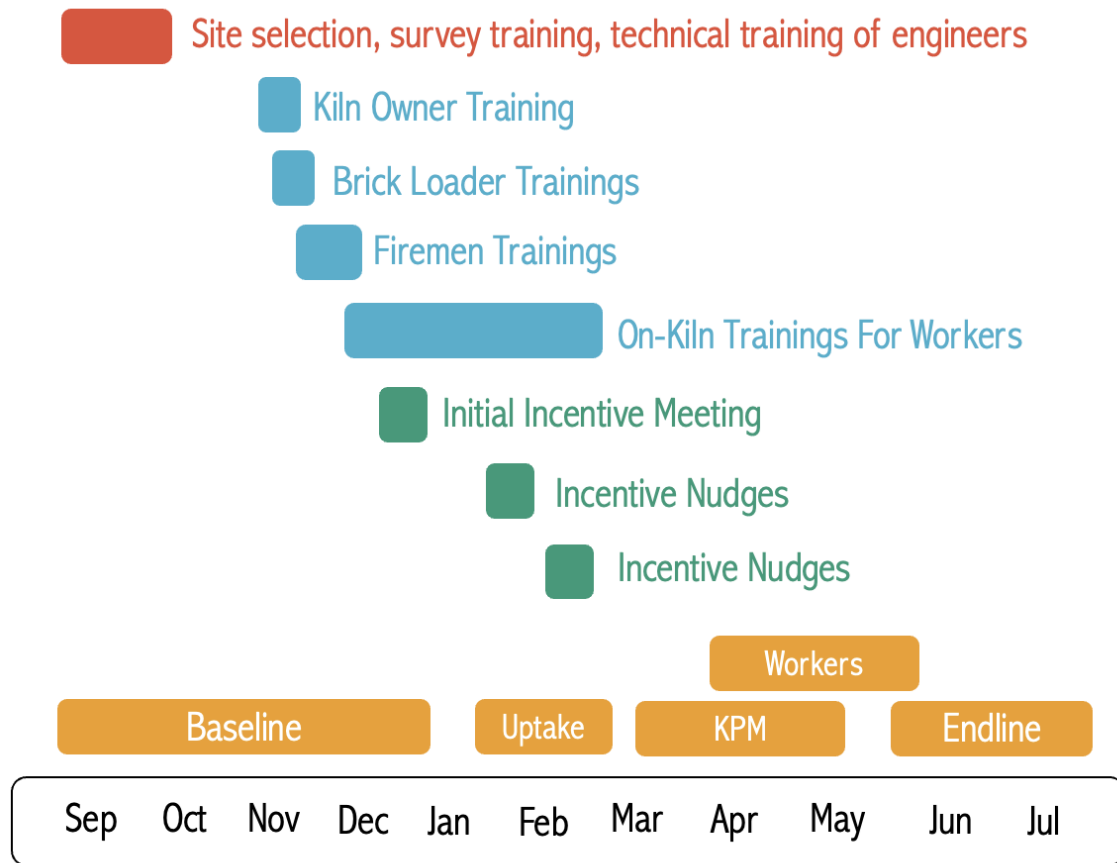

**Fig. S14.** Minimum Detectable Effect Sizes for RCT Outcomes. This figure presents the minimum detectable effect sizes for three outcomes (Class-1 bricks, CO/CO<sub>2</sub>, and specific energy consumption) estimated with the power calculations conducted prior to the study implementation. Based on these power calculations, we aimed to enroll 300 kilns total (100 per arm) to be powered to detect effects with 80% power. See [Materials and Methods](#) for details.

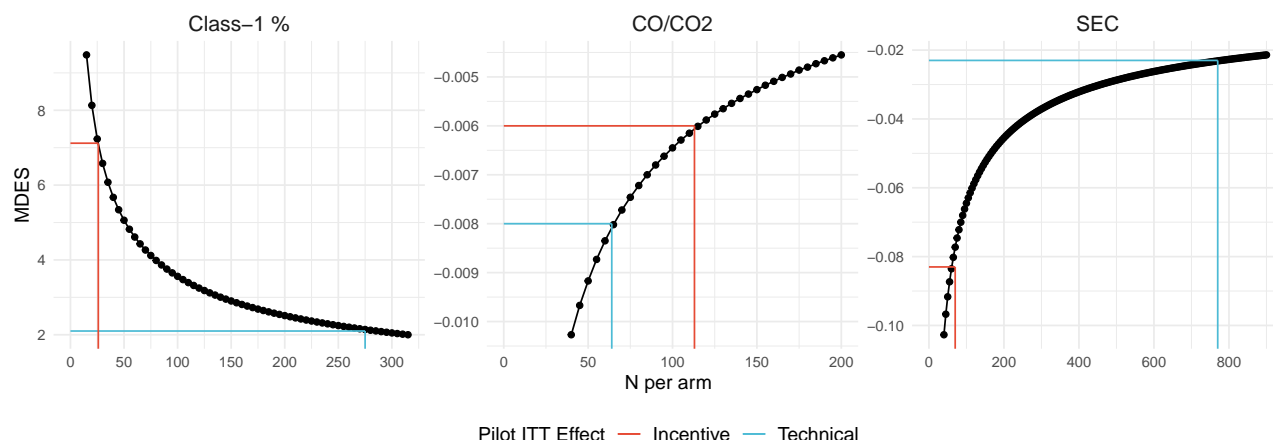

**Fig. S15.** Circuit-wise variation in the number of days required to complete the circuit and specific fuel consumption. This figure depicts the fuel requirements (per 100,000 bricks) across the brick firing season. At the beginning of the season (November-December), efficiency is lowest and then reaches a steady state around February.

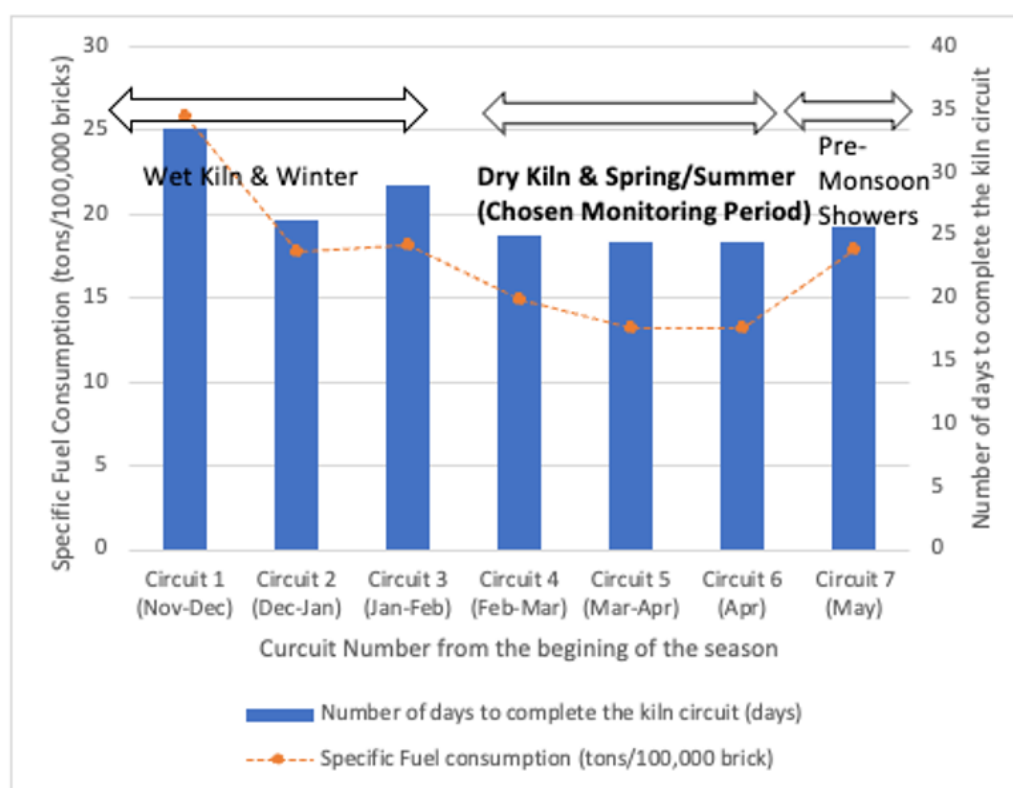

## Supplementary Tables

**Table S1.** Adoption By Intervention Component

	Adopter	Stacking	Feeding	Ash Layer	Cavity Wall	Sawdust	Total Practices
Technical Arm	0.45*** (0.06)	0.42*** (0.06)	0.45*** (0.06)	0.05 (0.05)	0.05 (0.05)	-0.02 (0.06)	0.95*** (0.17)
Technical+ Arm	0.44*** (0.06)	0.44*** (0.06)	0.44*** (0.06)	0.09* (0.05)	0.07 (0.05)	-0.10+ (0.06)	0.95*** (0.16)
N	276	276	276	276	276	276	276

+  $p < 0.1$ , \*  $p < 0.05$ , \*\*  $p < 0.01$ , \*\*\*  $p < 0.001$

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regression includes randomization strata fixed effects. Adoption (column 1) is defined as adopting both the improved stacking (column 2) and improved coal feeding (column 3) practices.

**Table S2.** Interaction between control and treatment kilns

Characteristic	N	Value
<b>How control kilns learned about intervention</b>		
Owner's association	18	78% (14)
Intervention team	18	39% (7)
Another kiln owner	18	67% (12)
Friend or relative	18	5.6% (1)
Another kiln worker	18	5.6% (1)
<b>Who control kilns requested support from</b>		
Another kiln's loading team	18	33% (6)
Intervention team	18	28% (5)
Another kiln's firing team	18	22% (4)
Another kiln owner	18	17% (3)
<b>Treatment kilns contact</b>		
Contacted about intervention	184	30% (55)
Provided support to adopt intervention	184	30% (56)

*Note:* This table presents summary statistics, % (n), for how control kiln adopters (n = 18) learned about the intervention and requested technical support. This table also presents summary statistics for whether intervention kilns (n = 184) were contacted about the intervention.

**Table S3.** Summary of Outcomes By Treatment Arm

Outcome	Control	Technical+	Technical
Specific Fuel Consumption (tons/100,000 bricks)	16.1 (3.3)	14.2 (3.0)	14.2 (2.7)
Specific Energy Consumption (MJ/kg fired brick)	1.07 (0.20)	0.94 (0.18)	0.95 (0.18)
CO/CO <sub>2</sub> (Mean ratio)	0.032 (0.014)	0.031 (0.018)	0.030 (0.016)
CO <sub>2</sub> Emissions (tons/season)	1,903 (505)	1,725 (428)	1,757 (368)
PM <sub>2.5</sub> (kg/season)	5.02 (1.33)	4.55 (1.13)	4.64 (0.97)
Value of Production (BDT/brick)	10.44 (0.19)	10.62 (0.20)	10.61 (0.21)
Fuel Spending (BDT/brick)	3.74 (0.71)	3.37 (0.66)	3.26 (0.77)
Total Fuel Costs (million BDT)	22.7 (5.9)	21.0 (5.3)	20.3 (5.1)
Annual Production (100,000 bricks)	62 (15)	63 (13)	63 (12)
Circuits Completed (Total number)	5.01 (1.31)	5.09 (1.19)	5.18 (1.11)
Class 1 (%)	78 (7)	84 (7)	84 (7)
Class 1.5 (%)	4.1 (4.6)	3.9 (5.8)	3.4 (3.9)
Class 2 (%)	8.2 (3.7)	4.9 (3.5)	5.0 (3.2)
Class 3 (%)	6.5 (3.6)	3.9 (3.4)	4.1 (3.6)
Broken Bricks (%)	3.24 (2.12)	3.07 (1.94)	3.19 (2.57)
Any benefits: any worker	74 (80%)	77 (81%)	70 (79%)
Any benefits: firing team	74 (80%)	76 (80%)	69 (78%)
Any benefits: loading team	37 (40%)	34 (36%)	36 (40%)
Any meals provided	75 (82%)	76 (80%)	77 (87%)
Cooking fuel provided	67 (73%)	79 (83%)	73 (82%)
Rest shed provided	83 (90%)	88 (93%)	79 (89%)
N	92	95	89

*Note:* This table presents the outcome means (standard deviations) by study arm. The first column presents the baseline mean and standard deviation in the Control arm, the second column presents the baseline mean and standard deviation in the Technical+ Arm, and the third column presents the baseline mean and standard deviation in the Technical Arm. The sample includes the 276 kilns for which outcome data was collected.

## Balance Tests

**Table S4.** Original Sample Results (N = 328)

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	14.1	8.2	15.5	10.1	14.3	9.7	0.82	0.4	0.25
Jashore Intervention Knowledge	0.29	0.46	0.32	0.47	0.28	0.45	0.98	0.57	0.55
Jashore Owner Interaction	0.48	0.51	0.50	0.51	0.61	0.50	0.69	0.79	0.86
Zigzag Year	2015	4	2014	4	2014	4	0.62	0.67	0.36
Water Adjacent	0.62	0.49	0.60	0.49	0.62	0.49	0.96	0.79	0.84
Bricks Fired (Lakhs)	8.0	1.0	8.0	1.2	8.0	1.2	0.8	0.89	0.68
Circuits Completed	5.9	1.6	5.8	1.5	5.9	1.8	0.76	0.61	0.37
Class 1 Production Share (%)	64.6	11.4	65.9	10.5	64.9	10.8	0.85	0.33	0.26
Production Cost Estimate BDT (per 1K Bricks)	8,754.4	1,155.4	8,529.8	1,192.9	8,666.2	1,032.8	0.51	0.36	0.14
Fired Brick Weight (kg)	3.37	0.25	3.41	0.22	3.41	0.23	0.19	0.98	0.2
Total Workers	108.6	27.8	107.8	31.5	109.3	34.2	0.91	0.74	0.81
Higher Secondary+	0.60	0.49	0.61	0.49	0.60	0.49	0.97	0.87	0.9
Highland	0.72	0.45	0.72	0.45	0.72	0.45	0.99	0.97	0.96
Joint Ownership	0.31	0.47	0.34	0.48	0.37	0.49	0.34	0.68	0.58
Shared Sardar	0.12	0.32	0.13	0.34	0.14	0.35	0.57	0.82	0.73
	N = 112		N = 108		N = 108				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the original 328 kilns enrolled in the study.



**Table S5.** Jashore Expansion Sample Results (N = 29)

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	17.0	6.4	17.2	8.5	20.9	10.3	0.38	0.39	0.97
Jashore Intervention Knowledge	1.0	0.0	0.73	0.47	1.0	0.0	0.28	0.066	0.05
Jashore Owner Interaction	0.33	0.50	0.62	0.52	0.33	0.50	0.94	0.32	0.36
Zigzag Year	2014	2	2015	2	2014	2	0.61	0.49	0.22
Water Adjacent	0.44	0.53	0.64	0.50	0.67	0.50	0.2	0.9	0.14
Bricks Fired (Lakhs)	7.83	0.61	7.4	1.3	8.00	0.75	0.61	0.18	0.3
Circuits Completed	6.4	1.4	6.5	1.5	6.4	1.7	0.81	1.0	0.84
Class 1 Production Share (%)	69.4	1.7	68.6	4.5	68.9	4.9	0.15	0.52	0.053
Production Cost Estimate BDT (per 1K Bricks)	9,055.6	300.5	9,000.0	591.6	9,044.4	133.3	0.94	0.83	0.82
Fired Brick Weight (kg)	3.37	0.11	3.38	0.11	3.34	0.13	0.68	0.58	0.89
Total Workers	98.0	29.3	117.5	26.5	98.2	28.8	0.99	0.15	0.17
Higher Secondary+	0.56	0.53	0.45	0.52	0.33	0.50	0.41	0.58	0.73
Highland	0.89	0.33	0.73	0.47	0.89	0.33	0.86	0.34	0.28
Joint Ownership	0.33	0.50	0.18	0.40	0.44	0.53	0.69	0.22	0.42
	N = 9		N = 11		N = 9				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the additional 29 kilns enrolled to meet sample size requirements.

**Table S6. Combined Sample Results (N = 357)**

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	14.3	8.1	15.7	9.9	14.8	9.8	0.62	0.53	0.23
Jashore Intervention Knowledge	0.36	0.48	0.37	0.49	0.36	0.48	0.94	0.84	0.77
Jashore Owner Interaction	0.44	0.50	0.53	0.51	0.53	0.51	0.78	0.68	0.51
Zigzag Year	2015	3	2014	4	2014	4	0.68	0.77	0.48
Water Adjacent	0.60	0.49	0.61	0.49	0.62	0.49	0.68	0.83	0.84
Bricks Fired (Lakhs)	8.0	1.0	8.0	1.2	8.0	1.2	0.74	0.81	0.94
Circuits Completed	6.0	1.6	5.8	1.5	5.9	1.8	0.76	0.67	0.42
Class 1 Production Share (%)	64.9	11.1	66.2	10.1	65.2	10.5	0.95	0.37	0.36
Production Cost Estimate BDT (per 1K Bricks)	8,776.8	1,116.8	8,573.3	1,157.1	8,695.3	997.6	0.5	0.36	0.14
Fired Brick Weight (kg)	3.37	0.24	3.41	0.21	3.40	0.22	0.22	0.94	0.19
Total Workers	107.8	27.9	108.6	31.1	108.5	33.9	0.93	0.95	0.88
Higher Secondary+	0.60	0.49	0.60	0.49	0.58	0.50	0.75	0.78	0.97
Highland	0.74	0.44	0.72	0.45	0.74	0.44	0.97	0.75	0.72
Joint Ownership	0.31	0.47	0.33	0.47	0.38	0.49	0.29	0.44	0.78
Shared Sardar	0.11	0.31	0.12	0.32	0.13	0.34	0.58	0.81	0.74
	N = 121		N = 119		N = 117				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the combined 357 kilns enrolled (original 328 kilns plus additional 28 kilns added in Jashore district).

**Table S7. Operated Sample Results (N = 340)**

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	14.4	8.1	15.6	9.9	14.8	9.9	0.69	0.6	0.32
Jashore Intervention Knowledge	0.36	0.48	0.37	0.48	0.37	0.49	0.77	0.86	0.92
Jashore Owner Interaction	0.42	0.50	0.53	0.51	0.53	0.51	0.79	0.67	0.5
Zigzag Year	2015	3	2014	4	2014	4	0.47	0.86	0.4
Water Adjacent	0.61	0.49	0.61	0.49	0.63	0.48	0.66	0.87	0.78
Bricks Fired (Lakhs)	8.01	0.98	7.9	1.2	8.0	1.2	0.94	0.44	0.36
Circuits Completed	6.0	1.6	5.9	1.5	6.0	1.8	0.92	0.86	0.77
Class 1 Production Share (%)	64.8	11.1	66.6	8.8	65.5	10.5	0.88	0.19	0.17
Production Cost Estimate BDT (per 1K Bricks)	8,788.1	1,126.2	8,578.0	1,203.8	8,674.1	999.8	0.36	0.54	0.16
Fired Brick Weight (kg)	3.38	0.24	3.41	0.21	3.40	0.22	0.43	0.79	0.3
Total Workers	107.4	27.7	109.2	31.5	109.2	33.7	0.78	0.92	0.69
Higher Secondary+	0.59	0.49	0.58	0.50	0.57	0.50	0.6	0.82	0.77
Highland	0.73	0.45	0.72	0.45	0.73	0.45	0.99	0.77	0.77
Joint Ownership	0.31	0.47	0.32	0.47	0.38	0.49	0.3	0.4	0.86
Shared Sardar	0.11	0.31	0.11	0.32	0.13	0.34	0.58	0.64	0.93
	N = 118		N = 108		N = 114				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the 340 kilns that were operated during the 2022-2023 firing season (out of 357 originally enrolled).

**Table S8.** No Government Interference Sample Results (N = 348)

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	14.4	8.2	15.6	9.9	14.8	9.9	0.66	0.57	0.28
Jashore Intervention Knowledge	0.38	0.49	0.38	0.49	0.35	0.48	0.87	0.78	0.9
Jashore Owner Interaction	0.44	0.50	0.52	0.51	0.52	0.51	0.79	0.68	0.51
Zigzag Year	2015	3	2014	4	2014	4	0.69	0.69	0.43
Water Adjacent	0.59	0.49	0.59	0.49	0.62	0.49	0.68	0.83	0.84
Bricks Fired (Lakhs)	8.0	1.0	8.0	1.2	8.0	1.2	0.7	0.71	1.0
Circuits Completed	6.0	1.6	5.8	1.5	5.9	1.8	0.82	0.53	0.36
Class 1 Production Share (%)	65.2	10.9	66.3	10.0	65.2	10.5	0.92	0.36	0.45
Production Cost Estimate BDT (per 1K Bricks)	8,773.4	1,123.6	8,558.4	1,174.4	8,684.1	994.5	0.44	0.38	0.13
Fired Brick Weight (kg)	3.37	0.24	3.41	0.22	3.40	0.22	0.26	0.86	0.21
Total Workers	107.1	28.1	108.1	30.4	108.2	33.9	0.84	0.98	0.86
Higher Secondary+	0.59	0.49	0.59	0.49	0.58	0.50	0.74	0.77	0.97
Highland	0.74	0.44	0.73	0.45	0.73	0.44	0.96	0.8	0.83
Joint Ownership	0.32	0.47	0.33	0.47	0.38	0.49	0.26	0.4	0.77
Shared Sardar	0.1	0.3	0.11	0.32	0.12	0.33	0.64	0.89	0.73
	N = 117		N = 115		N = 116				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the 348 kilns that remained open during the 2022-2023 firing season and were not shutdown by the government (out of 357 originally enrolled).

**Table S9.** Analytic Sample Results (N = 276)

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	15.4	8.5	16.5	10.1	14.6	9.7	0.64	0.26	0.46
Jashore Intervention Knowledge	0.37	0.49	0.37	0.49	0.36	0.48	0.82	0.91	0.92
Jashore Owner Interaction	0.44	0.51	0.58	0.50	0.52	0.51	0.77	0.48	0.33
Zigzag Year	2015	4	2014	4	2014	3	0.96	0.22	0.2
Water Adjacent	0.60	0.49	0.62	0.49	0.63	0.49	0.45	0.92	0.4
Bricks Fired (Lakhs)	8.0	1.0	7.9	1.2	8.1	1.1	0.36	0.12	0.45
Circuits Completed	6.1	1.5	6.0	1.5	6.1	1.8	0.9	0.59	0.45
Class 1 Production Share (%)	65.4	11.0	67.2	8.3	65.8	10.3	0.84	0.087	0.18
Production Cost Estimate BDT (per 1K Bricks)	8,810.4	1,215.1	8,581.1	1,284.3	8,683.2	1,039.5	0.29	0.77	0.22
Fired Brick Weight (kg)	3.38	0.24	3.40	0.19	3.39	0.23	0.56	0.85	0.43
Total Workers	107.9	28.9	111.2	31.5	110.8	34.8	0.75	0.67	0.46
Higher Secondary+	0.60	0.49	0.56	0.50	0.53	0.50	0.14	0.45	0.49
Highland	0.72	0.45	0.71	0.46	0.72	0.45	0.83	0.73	0.58
Joint Ownership	0.32	0.47	0.31	0.47	0.37	0.49	0.46	0.35	0.83
Shared Sardar	0.11	0.31	0.11	0.32	0.11	0.31	0.68	0.99	0.66
	N = 95		N = 89		N = 92				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the 276 kilns with outcome data collected for analysis.

**Table S10.** Attrition Tests

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Exclusive Firewood Use	0.13	0.34	0.11	0.31	0.15	0.35	0.76	0.42	0.62
Not Operated This Season	0.025	0.156	0.092	0.291	0.026	0.159	0.98	0.028	0.029
Not Operated or Exclusive Firewood Use	0.16	0.37	0.2	0.4	0.17	0.38	0.79	0.45	0.29
Demolished or Stopped by Gov	0.033	0.180	0.034	0.181	0.0085	0.0925	0.16	0.16	1.0
Dropped out (all reasons)	0.21	0.41	0.25	0.44	0.21	0.41	0.93	0.4	0.46

*Note:* This table presents the results of attrition tests run on the various reasons kilns dropped out of the study sample. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the 357 originally enrolled in the study.

## Arm-Specific Regression Results

**Table S11.** Specific Energy Consumption (MJ/kg fired brick)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.25*** (0.05)	-0.22*** (0.05)	-0.27*** (0.06)
Bundled Treatment		-0.11*** (0.02)			
Technical Arm	-0.10*** (0.03)				
Technical+ Arm	-0.12*** (0.03)				
Control Mean	1.07	1.07	1.07	1.07	1.07
Percent Change	-9.4% (T) -11.5% (T+)	-10.5%	-23.5%	-20.9%	-25.5%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S12.** CO<sub>2</sub> Emissions (tons)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-382.26** (140.86)	-339.39* (146.36)	-409.54* (161.82)
Bundled Treatment		-170.70** (60.05)			
Technical Arm	-153.12* (64.46)				
Technical+ Arm	-187.51** (68.27)				
Control Mean	1903.12	1903.12	1903.12	1903.12	1903.12
Percent Change	-8.0% (T) -9.9% (T+)	-9.0%	-20.1%	-17.8%	-21.5%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.



**Table S13. PM<sub>2.5</sub> Emissions (tons)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-1.01** (0.37)	-0.90* (0.39)	-1.08* (0.43)
Bundled Treatment		-0.45** (0.16)			
Technical Arm	-0.40* (0.17)				
Technical+ Arm	-0.50** (0.18)				
Control Mean	5.02	5.02	5.02	5.02	5.02
Percent Change	-8.0% (T) -9.9% (T+)	-9.0%	-20.1%	-17.8%	-21.5%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S14. Fuel Costs (BDT/brick)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.81*** (0.17)	-0.91*** (0.21)	-0.69*** (0.18)
Bundled Treatment		-0.36*** (0.08)			
Technical Arm	-0.41*** (0.10)				
Technical+ Arm	-0.31*** (0.09)				
Control Mean	3.74	3.74	3.74	3.74	3.74
Percent Change	-11.1% (T) -8.2% (T+)	-9.6%	-21.6%	-24.2%	-18.4%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S15.** Total Fuel Costs (million BDT)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-4.35** (1.64)	-5.02** (1.84)	-3.43+ (1.84)
Bundled Treatment		-1.94** (0.71)			
Technical Arm	-2.33** (0.79)				
Technical+ Arm	-1.57+ (0.80)				
Control Mean	22.71	22.71	22.71	22.71	22.71
Percent Change	-10.3% (T) -6.9% (T+)	-8.5%	-19.2%	-22.1%	-15.1%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S16.** Class 1 Bricks (%)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			0.142*** (0.016)	0.140*** (0.017)	0.143*** (0.020)
Bundled Treatment		0.063*** (0.009)			
Technical Arm	0.062*** (0.010)				
Technical+ Arm	0.064*** (0.010)				
Control Mean	0.78	0.78	0.78	0.78	0.78
Percent Change	8.0% (T) 8.2% (T+)	8.1%	18.2%	17.9%	18.3%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S17.** Endline Total Value of Production (BDT)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			36.70 (40.60)	41.99 (44.23)	36.26 (47.57)
Bundled Treatment		16.36 (18.54)			
Technical Arm	17.75 (20.49)				
Technical+ Arm	15.04 (21.15)				
Control Mean	639.41	639.41	639.41	639.41	639.41
Percent Change	2.8% (T) 2.4% (T+)	2.6%	5.7%	6.6%	5.7%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from kiln owner self-reports at endline. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S18.** Specific Fuel Consumption (tons/100,000 bricks)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-4.13*** (0.91)	-4.27*** (0.97)	-4.00*** (1.08)
Bundled Treatment		-1.84*** (0.41)			
Technical Arm	-1.91*** (0.42)				
Technical+ Arm	-1.77*** (0.46)				
Control Mean	15.97	15.97	15.97	15.97	15.97
Percent Change	-12.0% (T) -11.1% (T+)	-11.5%	-25.8%	-26.7%	-25.0%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S19.** Specific Coal Consumption (tons/100,000 bricks)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-2.49*** (0.67)	-2.42** (0.74)	-2.45** (0.79)
Bundled Treatment		-1.11*** (0.32)			
Technical Arm	-1.11** (0.35)				
Technical+ Arm	-1.11** (0.37)				
Control Mean	14.54	14.54	14.54	14.54	14.54
Percent Change	-7.6% (T) -7.6% (T+)	-7.6%	-17.1%	-16.7%	-16.9%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S20.** Endline Fuel Costs Per Brick (BDT/brick)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.28 (0.19)	-0.29 (0.19)	-0.31 (0.23)
Bundled Treatment		-0.13 (0.09)			
Technical Arm	-0.13 (0.09)				
Technical+ Arm	-0.13 (0.10)				
Control Mean	3.93	3.93	3.93	3.93	3.93
Percent Change	-3.2% (T) -3.2% (T+)	-3.2%	-7.2%	-7.4%	-7.9%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from kiln owner self-reports at endline. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S21.** Coal Costs (BDT/brick)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.72*** (0.18)	-0.78*** (0.21)	-0.63** (0.20)
Bundled Treatment		-0.32*** (0.08)			
Technical Arm	-0.36*** (0.10)				
Technical+ Arm	-0.28** (0.10)				
Control Mean	3.65	3.65	3.65	3.65	3.65
Percent Change	-9.8% (T) -7.7% (T+)	-8.7%	-19.6%	-21.4%	-17.2%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S22.** Total Coal Costs (million BDT)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-3.74* (1.65)	-4.27* (1.81)	-2.94 (1.91)
Bundled Treatment		-1.67* (0.72)			
Technical Arm	-1.99* (0.79)				
Technical+ Arm	-1.35 (0.84)				
Control Mean	22.11	22.11	22.11	22.11	22.11
Percent Change	-9.0% (T) -6.1% (T+)	-7.5%	-16.9%	-19.3%	-13.3%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S23.** Mean CO/CO<sub>2</sub> Ratio

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0020 (0.0039)	-0.0032 (0.0045)	-0.0004 (0.0048)
Bundled Treatment		-0.0009 (0.0018)			
Technical Arm	-0.0014 (0.0021)				
Technical+ Arm	-0.0004 (0.0021)				
Control Mean	0.03	0.03	0.03	0.03	0.03
Percent Change	-4.5% (T) -1.3% (T+)	-2.8%	-6.4%	-10.2%	-1.2%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S24.** Annual Production (100,000 bricks)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			1.77 (3.84)	2.31 (4.16)	1.80 (4.50)
Bundled Treatment		0.79 (1.73)			
Technical Arm	0.89 (1.91)				
Technical+ Arm	0.69 (1.98)				
Control Mean	61.52	61.52	61.52	61.52	61.52
Percent Change	1.4% (T) 1.1% (T+)	1.3%	2.9%	3.7%	2.9%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.



**Table S25. Circuits Completed (Total number)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			0.18 (0.34)	0.16 (0.38)	0.16 (0.40)
Bundled Treatment		0.08 (0.15)			
Technical Arm	0.09 (0.17)				
Technical+ Arm	0.07 (0.17)				
Control Mean	5.01	5.01	5.01	5.01	5.01
Percent Change	1.8% (T) 1.4% (T+)	1.6%	3.6%	3.2%	3.2%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S26. Total Value of Production (BDT)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			42.84 (40.53)	47.82 (44.15)	43.99 (47.62)
Bundled Treatment		19.10 (18.56)			
Technical Arm	19.87 (20.52)				
Technical+ Arm	18.38 (21.22)				
Control Mean	642.66	642.66	642.66	642.66	642.66
Percent Change	3.1% (T) 2.9% (T+)	3.0%	6.7%	7.4%	6.8%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Total value of production is calculated by applying the objective brick quality data measured during the kiln performance assessment to the annual production reported at endline. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S27.** Value of Production Per Brick (BDT/brick)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			0.39*** (0.04)	0.38*** (0.05)	0.41*** (0.05)
Bundled Treatment		0.18*** (0.02)			
Technical Arm	0.17*** (0.03)				
Technical+ Arm	0.18*** (0.03)				
Control Mean	10.44	10.44	10.44	10.44	10.44
Percent Change	1.6% (T) 1.8% (T+)	1.7%	3.8%	3.6%	3.9%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S28.** Endline Value Per Brick (BDT)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			0.30*** (0.05)	0.29*** (0.06)	0.29*** (0.06)
Bundled Treatment		0.13*** (0.03)			
Technical Arm	0.14*** (0.03)				
Technical+ Arm	0.13*** (0.03)				
Control Mean	10.38	10.38	10.38	10.38	10.38
Percent Change	1.3% (T) 1.3% (T+)	1.3%	2.9%	2.8%	2.8%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from kiln owner self-reports at endline. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S29. Total Value of Production (BDT)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			42.84 (40.53)	47.82 (44.15)	43.99 (47.62)
Bundled Treatment		19.10 (18.56)			
Technical Arm	19.87 (20.52)				
Technical+ Arm	18.38 (21.22)				
Control Mean	642.66	642.66	642.66	642.66	642.66
Percent Change	3.1% (T) 2.9% (T+)	3.0%	6.7%	7.4%	6.8%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Total value of production is calculated by applying the objective brick quality data measured during the kiln performance assessment to the annual production reported at endline. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S30. Endline Class 1 Bricks (%)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			0.11*** (0.02)	0.11*** (0.02)	0.11*** (0.02)
Bundled Treatment		0.05*** (0.01)			
Technical Arm	0.05*** (0.01)				
Technical+ Arm	0.05*** (0.01)				
Control Mean	0.76	0.76	0.76	0.76	0.76
Percent Change	6.7% (T) 6.4% (T+)	6.5%	14.6%	14.1%	14.3%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from kiln owner self-reports at endline. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S31.** Endline Specific Fuel Consumption (tons/100,000 bricks)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-3.04** (1.04)	-2.86** (1.08)	-3.46** (1.27)
Bundled Treatment		-1.36** (0.46)			
Technical Arm	-1.24** (0.47)				
Technical+ Arm	-1.47** (0.52)				
Control Mean	17.27	17.27	17.27	17.27	17.27
Percent Change	-7.2% (T) -8.5% (T+)	-7.9%	-17.6%	-16.6%	-20.0%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from kiln owner self-reports at endline. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S32.** Heterogeneous Treatment Effects

	Specific Energy Consumption			Class 1 Bricks (%)		
	Experience	Education	Location	Experience	Education	Location
Bundled Treatment	-0.07	-0.08*	-0.10*	0.04**	0.07***	0.06***
	(0.04)	(0.03)	(0.04)	(0.01)	(0.01)	(0.01)
Owner Experience	0.00			0.00		
	(0.00)			(0.00)		
Treatment X Owner Experience	-0.00			0.00		
	(0.00)			(0.00)		
Higher Secondary+		0.02			0.02	
		(0.04)			(0.02)	
Treatment X Higher Secondary+		-0.06			-0.02	
		(0.05)			(0.02)	
Highland			-0.02			0.01
			(0.05)			(0.02)
Treatment X Highland			-0.02			-0.00
			(0.05)			(0.02)
N	276	276	276	276	276	276

+  $p < 0.1$ , \*  $p < 0.05$ , \*\*  $p < 0.01$ , \*\*\*  $p < 0.001$

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regression includes randomization strata fixed effects. Kiln characteristics (owner experience, education, and kiln location) are from baseline data and outcomes are derived from the kiln performance monitoring. Kiln owner experience is measured in years, higher secondary+ is a binary indicator that equals 1 if the owner has attained higher secondary schooling or more, and highland indicates a kiln is located on highland (as opposed to lowland).

## Changes In Other Costs

**Table S33. Sawdust Spending (BDT/ton)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-4940.88* (2081.33)	-4543.22* (2132.59)	-5683.20* (2483.10)
Bundled Treatment		-2206.90* (886.32)			
Technical Arm	-1921.35* (914.09)				
Technical+ Arm	-2479.92* (956.84)				
Control Mean	3573.64	3573.64	3573.64	3573.64	3573.64
Percent Change	-53.8% (T) -69.4% (T+)	-61.8%	-138.3%	-127.1%	-159.0%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during endline and kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S34. Soil (BDT per 1000 bricks)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			27.43 (28.60)	0.88 (33.02)	52.79 (34.87)
Bundled Treatment		12.34 (12.64)			
Technical Arm	1.59 (14.89)				
Technical+ Arm	22.62 (15.36)				
Control Mean	902.3	902.3	902.3	902.3	902.3
Percent Change	0.2% (T) 2.5% (T+)	1.4%	3.0%	0.1%	5.9%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during endline and kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.



**Table S35. Molding (BDT per 1000 bricks)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			9.89 (32.69)	10.17 (39.35)	9.02 (37.92)
Bundled Treatment		4.39 (14.54)			
Technical Arm	6.58 (17.36)				
Technical+ Arm	2.30 (16.59)				
Control Mean	1026.79	1026.79	1026.79	1026.79	1026.79
Percent Change	0.6% (T) 0.2% (T+)	0.4%	1.0%	1.0%	0.9%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during endline and kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S36. Coal preparation (BDT per season)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			17494.21 (16369.83)	31382.76 (19278.21)	4816.06 (18556.09)
Bundled Treatment		7750.48 (7400.13)			
Technical Arm	13239.60 (8852.78)				
Technical+ Arm	2502.05 (8255.78)				
Control Mean	214463.91	214463.91	214463.91	214463.91	214463.91
Percent Change	6.2% (T) 1.2% (T+)	3.6%	8.2%	14.6%	2.2%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during endline and kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S37. Brick loading (BDT per 1000 bricks)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			13.59 (11.50)	9.55 (12.81)	16.67 (13.51)
Bundled Treatment		6.07 (5.10)			
Technical Arm	5.85 (5.81)				
Technical+ Arm	6.27 (5.90)				
Control Mean	307.52	307.52	307.52	307.52	307.52
Percent Change	1.9% (T) 2.0% (T+)	2.0%	4.4%	3.1%	5.4%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during endline and kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S38. Firemen cost (BDT per season)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			45656.58 (43496.33)	37695.26 (49501.40)	63099.23 (49902.29)
Bundled Treatment		20386.10 (19625.66)			
Technical Arm	18452.90 (22541.56)				
Technical+ Arm	22234.53 (22297.62)				
Control Mean	1069347.83	1069347.83	1069347.83	1069347.83	1069347.83
Percent Change	1.7% (T) 2.1% (T+)	1.9%	4.3%	3.5%	5.9%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during endline and kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S39.** Brick unloading (BDT per 1000 bricks)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			8.35 (8.94)	7.80 (10.45)	8.23 (10.34)
Bundled Treatment		3.73 (3.98)			
Technical Arm	3.35 (4.63)				
Technical+ Arm	4.09 (4.54)				
Control Mean	204.54	204.54	204.54	204.54	204.54
Percent Change	1.6% (T) 2.0% (T+)	1.8%	4.1%	3.8%	4.0%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during endline and kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

## Supplementary CO/CO<sub>2</sub> Analysis

**Table S40.** Max CO/CO<sub>2</sub> Ratio

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0082 (0.0064)	-0.0112 (0.0074)	-0.0053 (0.0075)
Bundled Treatment		-0.0037 (0.0030)			
Technical Arm	-0.0048 (0.0035)				
Technical+ Arm	-0.0025 (0.0035)				
Control Mean	0.06	0.06	0.06	0.06	0.06
Percent Change	-8.6% (T) -4.5% (T+)	-6.5%	-14.7%	-19.9%	-9.5%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S41. SD CO/CO<sub>2</sub> Ratio**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0029* (0.0014)	-0.0030+ (0.0016)	-0.0031* (0.0016)
Bundled Treatment		-0.0013* (0.0007)			
Technical Arm	-0.0013+ (0.0008)				
Technical+ Arm	-0.0013+ (0.0007)				
Control Mean	0.01	0.01	0.01	0.01	0.01
Percent Change	-14.2% (T) -14.4% (T+)	-14.3%	-32.1%	-32.3%	-33.7%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S42. IQR CO/CO<sub>2</sub> Ratio**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0035 (0.0022)	-0.0033 (0.0025)	-0.0040 (0.0025)
Bundled Treatment		-0.0016 (0.0010)			
Technical Arm	-0.0015 (0.0011)				
Technical+ Arm	-0.0016 (0.0011)				
Control Mean	0.01	0.01	0.01	0.01	0.01
Percent Change	-12.3% (T) -13.4% (T+)	-12.9%	-28.9%	-27.6%	-33.4%
N	276	276	276	181	187

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding.

**Table S43.** Mean CO/CO<sub>2</sub>Ratio (dropping abnormal feeding)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0025 (0.0043)	-0.0039 (0.0049)	-0.0006 (0.0053)
Bundled Treatment		-0.0011 (0.0019)			
Technical Arm	-0.0015 (0.0022)				
Technical+ Arm	-0.0006 (0.0023)				
Control Mean	0.03	0.03	0.03	0.03	0.03
Percent Change	-4.8% (T) -1.9% (T+)	-3.3%	-7.7%	-12.1%	-2.0%
N	256	256	256	164	174

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with total feeding time below 33%, which indicates abnormal operation.

**Table S44.** Max CO/CO<sub>2</sub> Ratio (dropping abnormal feeding)

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0078 (0.0068)	-0.0108 (0.0079)	-0.0043 (0.0081)
Bundled Treatment		-0.0034 (0.0031)			
Technical Arm	-0.0046 (0.0036)				
Technical+ Arm	-0.0022 (0.0035)				
Control Mean	0.06	0.06	0.06	0.06	0.06
Percent Change	-8.2% (T) -4.0% (T+)	-6.0%	-14.1%	-19.4%	-7.7%
N	256	256	256	164	174

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with total feeding time below 33%, which indicates abnormal operation.

**Table S45. SD CO/CO<sub>2</sub> Ratio (dropping abnormal feeding)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0031* (0.0015)	-0.0031+ (0.0017)	-0.0030+ (0.0017)
Bundled Treatment		-0.0013+ (0.0007)			
Technical Arm	-0.0013+ (0.0008)				
Technical+ Arm	-0.0013+ (0.0007)				
Control Mean	0.01	0.01	0.01	0.01	0.01
Percent Change	-14.7% (T) -14.3% (T+)	-14.5%	-33.6%	-33.5%	-33.2%
N	256	256	256	164	174

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with total feeding time below 33%, which indicates abnormal operation.

**Table S46. IQR CO/CO<sub>2</sub> Ratio (dropping abnormal feeding)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0039+ (0.0023)	-0.0041+ (0.0024)	-0.0039 (0.0027)
Bundled Treatment		-0.0017+ (0.0010)			
Technical Arm	-0.0018+ (0.0011)				
Technical+ Arm	-0.0016 (0.0012)				
Control Mean	0.01	0.01	0.01	0.01	0.01
Percent Change	-15.0% (T) -13.0% (T+)	-14.0%	-32.5%	-33.6%	-32.1%
N	256	256	256	164	174

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with total feeding time below 33%, which indicates abnormal operation.

**Table S47. Mean CO/CO<sub>2</sub> Ratio (dropping abnormal values)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0023 (0.0039)	-0.0022 (0.0046)	-0.0016 (0.0048)
Bundled Treatment		-0.0011 (0.0018)			
Technical Arm	-0.0011 (0.0021)				
Technical+ Arm	-0.0010 (0.0022)				
Control Mean	0.03	0.03	0.03	0.03	0.03
Percent Change	-3.4% (T) -3.2% (T+)	-3.3%	-7.3%	-6.9%	-5.1%
N	264	264	264	171	181

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with O<sub>2</sub>, CO<sub>2</sub>, and CO outside normal ranges for more than 50% of the monitored time, which indicates abnormal operation.

**Table S48. Max CO/CO<sub>2</sub> Ratio (dropping abnormal values)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0097 (0.0064)	-0.0106 (0.0076)	-0.0085 (0.0075)
Bundled Treatment		-0.0044 (0.0030)			
Technical Arm	-0.0047 (0.0036)				
Technical+ Arm	-0.0041 (0.0035)				
Control Mean	0.06	0.06	0.06	0.06	0.06
Percent Change	-8.3% (T) -7.2% (T+)	-7.7%	-17.1%	-18.7%	-15.0%
N	264	264	264	171	181

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with O<sub>2</sub>, CO<sub>2</sub>, and CO outside normal ranges for more than 50% of the monitored time, which indicates abnormal operation.

**Table S49. SD CO/CO<sub>2</sub> Ratio (dropping abnormal values)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0032* (0.0014)	-0.0030+ (0.0017)	-0.0036* (0.0016)
Bundled Treatment		-0.0015* (0.0007)			
Technical Arm	-0.0013 (0.0008)				
Technical+ Arm	-0.0016* (0.0007)				
Control Mean	0.01	0.01	0.01	0.01	0.01
Percent Change	-14.2% (T) -17.1% (T+)	-15.7%	-34.7%	-32.4%	-39.1%
N	264	264	264	171	181

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with O<sub>2</sub>, CO<sub>2</sub>, and CO outside normal ranges for more than 50% of the monitored time, which indicates abnormal operation.

**Table S50. IQR CO/CO<sub>2</sub> Ratio (dropping abnormal values)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0033 (0.0023)	-0.0030 (0.0026)	-0.0039 (0.0026)
Bundled Treatment		-0.0015 (0.0011)			
Technical Arm	-0.0014 (0.0012)				
Technical+ Arm	-0.0016 (0.0012)				
Control Mean	0.01	0.01	0.01	0.01	0.01
Percent Change	-11.3% (T) -13.2% (T+)	-12.3%	-27.1%	-25.0%	-32.4%
N	264	264	264	171	181

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with O<sub>2</sub>, CO<sub>2</sub>, and CO outside normal ranges for more than 50% of the monitored time, which indicates abnormal operation.



**Table S51. Mean CO/CO<sub>2</sub> Ratio (dropping abnormal feeding & values)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0014 (0.0039)	-0.0019 (0.0045)	-0.0004 (0.0048)
Bundled Treatment		-0.0006 (0.0018)			
Technical Arm	-0.0008 (0.0021)				
Technical+ Arm	-0.0005 (0.0022)				
Control Mean	0.03	0.03	0.03	0.03	0.03
Percent Change	-2.6% (T) -1.4% (T+)	-2.0%	-4.4%	-5.9%	-1.3%
N	272	272	272	178	186

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with O<sub>2</sub>, CO<sub>2</sub>, CO outside normal ranges for more than 50% of the monitored time and with total feeding time below 33%, which indicates abnormal operation.

**Table S52. Max CO/CO<sub>2</sub> Ratio (dropping abnormal feeding & values)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0076 (0.0063)	-0.0092 (0.0074)	-0.0061 (0.0074)
Bundled Treatment		-0.0035 (0.0030)			
Technical Arm	-0.0040 (0.0035)				
Technical+ Arm	-0.0030 (0.0035)				
Control Mean	0.06	0.06	0.06	0.06	0.06
Percent Change	-7.1% (T) -5.3% (T+)	-6.2%	-13.7%	-16.4%	-10.9%
N	272	272	272	178	186

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with O<sub>2</sub>, CO<sub>2</sub>, CO outside normal ranges for more than 50% of the monitored time and with total feeding time below 33%, which indicates abnormal operation.

**Table S53. SD CO/CO<sub>2</sub> Ratio (dropping abnormal feeding & values)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0029* (0.0014)	-0.0026 (0.0017)	-0.0033* (0.0015)
Bundled Treatment		-0.0013* (0.0007)			
Technical Arm	-0.0012 (0.0008)				
Technical+ Arm	-0.0014* (0.0007)				
Control Mean	0.01	0.01	0.01	0.01	0.01
Percent Change	-12.7% (T) -15.6% (T+)	-14.2%	-31.5%	-28.7%	-35.5%
N	272	272	272	178	186

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with O<sub>2</sub>, CO<sub>2</sub>, CO outside normal ranges for more than 50% of the monitored time and with total feeding time below 33%, which indicates abnormal operation.

**Table S54. IQR CO/CO<sub>2</sub> Ratio (dropping abnormal feeding & values)**

	Intention-to-Treat (Separate)	Intention-to-Treat (Bundled)	Instrumental Variable	Instrumental Variable (Technical)	Instrumental Variable (Technical+)
Adopted Intervention			-0.0032 (0.0022)	-0.0028 (0.0025)	-0.0039 (0.0025)
Bundled Treatment		-0.0014 (0.0010)			
Technical Arm	-0.0013 (0.0011)				
Technical+ Arm	-0.0016 (0.0011)				
Control Mean	0.01	0.01	0.01	0.01	0.01
Percent Change	-10.6% (T) -13.2% (T+)	-11.9%	-26.4%	-23.2%	-32.1%
N	272	272	272	178	186

+ p < 0.1, \* p < 0.05, \*\* p < 0.01, \*\*\* p < 0.001

*Note:* Heteroskedasticity-robust standard errors are in parentheses. Regressions include randomization strata fixed effects. Outcome data are derived from measurements collected during kiln performance monitoring. Adoption is defined as adopting double/triple zigzag brick stacking and single fireman continuous feeding. Sample excludes kilns with O<sub>2</sub>, CO<sub>2</sub>, CO outside normal ranges for more than 50% of the monitored time and with total feeding time below 33%, which indicates abnormal operation.

**Table S55.** Above 33 Pct Fuel Feeding Sample Results (N = 255)

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	15.7	8.5	17.0	10.2	13.9	9.6	0.25	0.074	0.4
Jashore Intervention Knowledge	0.37	0.49	0.40	0.49	0.35	0.48	0.82	0.72	0.88
Jashore Owner Interaction	0.44	0.51	0.58	0.50	0.58	0.50	0.47	0.8	0.32
Zigzag Year	2015	4	2014	4	2015	3	0.58	0.055	0.17
Water Adjacent	0.61	0.49	0.60	0.49	0.62	0.49	0.6	1.0	0.6
Bricks Fired (Lakhs)	8.06	0.97	7.9	1.1	8.1	1.1	0.72	0.15	0.23
Circuits Completed	6.1	1.5	6.0	1.5	6.2	1.9	0.98	0.53	0.43
Class 1 Production Share (%)	65.3	10.6	67.1	8.3	65.4	10.4	0.42	0.031	0.24
Production Cost Estimate BDT (per 1K Bricks)	8,842.3	1,220.9	8,606.3	1,317.3	8,673.5	1,060.4	0.19	0.97	0.23
Fired Brick Weight (kg)	3.38	0.24	3.40	0.19	3.40	0.23	0.4	0.95	0.4
Total Workers	108.8	28.7	111.5	30.3	110.8	35.2	0.89	0.57	0.47
Higher Secondary+	0.60	0.49	0.57	0.50	0.56	0.50	0.27	0.47	0.72
Highland	0.72	0.45	0.73	0.45	0.69	0.46	0.48	0.73	0.74
Joint Ownership	0.32	0.47	0.29	0.46	0.38	0.49	0.32	0.18	0.68
Shared Sardar	0.11	0.31	0.12	0.33	0.099	0.300	0.91	0.64	0.55
	N = 92		N = 82		N = 81				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the 255 kilns with total feeding time above 33% (which indicates normal operation).

**Table S56.** Under 50 Out Of Range Sample Results (N = 264)

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	15.5	8.5	17.0	10.2	15.0	9.8	0.75	0.24	0.34
Jashore Intervention Knowledge	0.36	0.48	0.38	0.49	0.35	0.48	0.89	0.89	0.98
Jashore Owner Interaction	0.46	0.51	0.6	0.5	0.54	0.51	0.87	0.46	0.39
Zigzag Year	2015	4	2014	4	2014	4	0.9	0.2	0.24
Water Adjacent	0.61	0.49	0.64	0.48	0.64	0.48	0.48	0.73	0.3
Bricks Fired (Lakhs)	8.0	1.0	7.9	1.2	8.1	1.1	0.33	0.17	0.59
Circuits Completed	6.1	1.6	6.0	1.5	6.1	1.9	0.88	0.7	0.54
Class 1 Production Share (%)	65.1	10.9	67.5	8.2	66.0	10.3	0.98	0.071	0.11
Production Cost Estimate BDT (per 1K Bricks)	8,817.1	1,225.1	8,574.9	1,307.8	8,725.6	1,025.2	0.35	0.6	0.19
Fired Brick Weight (kg)	3.38	0.24	3.40	0.19	3.39	0.22	0.53	0.91	0.44
Total Workers	108.0	29.1	112.5	31.2	111.4	35.4	0.68	0.54	0.3
Higher Secondary+	0.60	0.49	0.59	0.49	0.53	0.50	0.11	0.21	0.75
Highland	0.71	0.46	0.72	0.45	0.72	0.45	0.93	0.84	0.76
Joint Ownership	0.32	0.47	0.30	0.46	0.36	0.48	0.55	0.29	0.63
Shared Sardar	0.11	0.31	0.12	0.33	0.11	0.32	0.61	0.88	0.49
	N = 93		N = 83		N = 88				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the 272 kilns with O<sub>2</sub>, CO<sub>2</sub>, CO outside normal ranges for less than 50% of the monitored time (which indicates normal operation).

**Table S57.** Under 50 Out Of Range Or Above 33 Pct Fuel Feeding Sample Results (N = 272)

Balance Variable	Technical+ Mean	Technical+ Std. Dev.	Technical Mean	Technical Std. Dev.	Control Mean	Control Std. Dev.	T+ - C (p-val)	T - C (p-val)	T+ - T (p-val)
Owner Experience (Years)	15.5	8.5	16.8	10.1	14.6	9.7	0.6	0.19	0.37
Jashore Intervention Knowledge	0.37	0.49	0.38	0.49	0.36	0.48	0.82	0.89	0.94
Jashore Owner Interaction	0.44	0.51	0.58	0.50	0.52	0.51	0.77	0.48	0.33
Zigzag Year	2015	4	2014	4	2014	3	0.99	0.17	0.17
Water Adjacent	0.61	0.49	0.62	0.49	0.63	0.49	0.52	0.85	0.42
Bricks Fired (Lakhs)	8.0	1.0	7.9	1.2	8.1	1.1	0.35	0.11	0.44
Circuits Completed	6.1	1.5	6.0	1.5	6.1	1.8	0.91	0.72	0.59
Class 1 Production Share (%)	65.2	10.9	67.3	8.3	65.8	10.3	0.88	0.084	0.17
Production Cost Estimate BDT (per 1K Bricks)	8,819.0	1,218.6	8,595.6	1,299.0	8,683.2	1,039.5	0.28	0.81	0.24
Fired Brick Weight (kg)	3.38	0.24	3.40	0.19	3.39	0.23	0.61	0.81	0.44
Total Workers	108.1	29.0	111.7	31.0	110.8	34.8	0.75	0.54	0.36
Higher Secondary+	0.60	0.49	0.58	0.50	0.53	0.50	0.14	0.26	0.75
Highland	0.71	0.45	0.73	0.45	0.72	0.45	0.87	0.91	0.78
Joint Ownership	0.32	0.47	0.30	0.46	0.37	0.49	0.49	0.26	0.65
Shared Sardar	0.11	0.31	0.12	0.32	0.11	0.31	0.68	0.84	0.53
	N = 94		N = 86		N = 92				

*Note:* This table presents the results of balance tests run on baseline characteristics. The first two columns present the baseline mean and standard deviation in the Technical+ Arm, the second two present the baseline mean and standard deviation in the Technical Arm, and the third two present the baseline mean and standard deviation in the Control Arm. The last three columns present the p-value for a t-test of the difference in means between (1) Technical+ and Control, (2) Technical and Control, and (3) Technical+ and Technical. T-tests control for the randomization strata. The sample includes the 272 kilns with O<sub>2</sub>, CO<sub>2</sub>, CO outside normal ranges for less than 50% of the monitored time and total feeding time above 33% (which indicates normal operation).

**Table S58.** Estimated Effect Sizes from Pilot Study

<b>Outcome</b>	<b>Control Group Mean</b>	<b>Technical ITT</b>	<b>Incentive ITT</b>	<b>TOT</b>
Class-1 (%)	66	2.1	7.12	9.22
CO/CO <sub>2</sub> (ratio)	0.04	-0.008	-0.006	-0.014
SEC (MJ/kg-fired brick)	1.28	-0.023	-0.083	-0.107

**Table S59.** Minimum Detectable Effect Sizes and Power for 100 kilns per arm

	<b>MDES</b>		<b>Power b/w treatment arms</b>
	Power: 0.9	Power: 0.8	
Class-1 (%)	3.56	3.08	0.81
CO/CO <sub>2</sub> (ratio)	-0.0064	-0.0056	0.19
SEC (MJ/kg-fired brick)	-0.065	-0.056	0.23

**Table S60.** Activity Schedule

<b>Day &amp; Time</b>	<b>Activity</b>
Day 1	
08:00	The two-member team and helpers with all necessary equipment and materials arrive at the brick kiln site.
08:00 – 09:00	Meet brick kiln manager and brief him on the key tasks the team will be performing over next 2 days and the support required from kiln management. After initial briefing, request that he introduce the team to loading and unloading supervisors and the head fireman/firing supervisor. Tour the kiln with the kiln manager. Find key information on the kiln through questions and observations:

*Continued on next page*

Table S60 – *Continued from previous page*

Day & Time	Activity
	<ul style="list-style-type: none"> <li>• Is the kiln's operation normal, or are there any operational issues—e.g. a shortage of workers, shortage of green bricks, etc.?</li> <li>• Observe the location of the fuel feeding/firing zone. The fuel feeding zone should be in the straight part of the kiln circuit. Check brick loading and unloading locations.</li> <li>• List the fuels being used.</li> <li>• How many chambers are being completed in a day (24-hour period)?</li> <li>• What is the approximate quantity of fuel used in 24 hours?</li> <li>• The type of brick setting and number of bricks loaded in one chamber.</li> <li>• Where is crushed fuel stored, and what is the quantity? Is there sufficient space for storing the weighed fuel for monitoring?</li> <li>• Time of the last chamber shifting and time when the next shifting is planned.</li> <li>• What is the typical schedule for the unloading operation, and where are unloaded bricks stacked?</li> </ul> <p>This is the basic information required for kiln monitoring, which can be used to fine tune the monitoring plan.</p>
09:00 onward	One team member, with assistance from workers, starts the process of weighing and storing fuel:

*Continued on next page*

Table S60 – *Continued from previous page*

Day & Time	Activity
	<ul style="list-style-type: none"> <li>• Using buckets of known volume and weight and a balance scale, individually weigh 5 buckets of each fuel and note the weight. Take the average of the 5 measurements to calculate the average weight of fuel/bucket and the density of each type of fuel.</li> <li>• Ask the kiln manager the amount of fuel required for 24 hours (also cross-check with your estimations). Calculate the number of buckets required of each fuel to obtain 1.1 times the 24-hour requirement.</li> <li>• Spread the tarpaulin on the ground.</li> <li>• Start the process of collecting the required quantities of fuel on the tarpaulin. This will require help from at least 2 workers and can take 3-4 hours. Use tokens to count the number of buckets.</li> <li>• When the fuel collection is complete, enter the initial quantity of each type of fuel on the ODK form.</li> <li>• Collect fuel samples in zip bags and label each with the number generated by the ODK, date of collection, and name of the fuel.</li> </ul>
09:00 onward	<p>The second team member prepares to start the 24-hour fuel consumption trial:</p> <ul style="list-style-type: none"> <li>• Observe kiln operations and complete Sections 1 to 4 on the ODK form.</li> <li>• Talk to firemen and coal persons and explain what the 24-hour fuel consumption trial will entail. Ask that they not add excess coal to containers/drums before the next chamber shifting.</li> <li>• Usually, a chamber shifting takes place sometime between 10:00 and 13:00 hrs. The aim should be to start the trial by lunchtime on day 1.</li> <li>• Supervise the start of the 24 hours fuel consumption trial.</li> </ul>
11:00 onward	<p>Ask the unloading sardar where they intend to stack fired bricks the next day and request that he organize the stacks so that it is easy to count the number of bricks. Check the unloading plan for the next day with him.</p>
14:00 – 18:00 hrs	<p>Carry out flue gas analysis (Option 1).</p>

*Continued on next page*



Table S60 – *Continued from previous page*

Day & Time	Activity
	<ul style="list-style-type: none"> <li>• Ensure that flue gas monitoring is not done immediately after the shifting of a chamber and that there is a gap of at least 1 hour.</li> <li>• The duration of flue gas monitoring is 2 hours. The total time required is close to 2.5 hours, which includes setting up the instrument and packing it after the measurements.</li> <li>• The measurements are collected at the shunt. Lift the shunt a few inches and place the pipe, which acts as the monitoring port. Insert and position the probe (at this point, the probe is not connected to the flue gas analyzer) inside the pipe. Ensure that there is no leakage of air from around the pipe by covering it with ash. Also ensure that the gap between the probe and the pipe is sealed with clay.</li> <li>• Switch on and self-calibrate the flue gas analyzer in open air. After self-calibration, connect the flue gas analyzer with the probe and ensure that the flue gas analyzer reading is displayed correctly on the computer tablet (using the KANE Live program). Flue gas analyzer readings are to be saved periodically both on the tablet and in the flue gas analyzer's memory. Ensure that the flue gas analyzer and the tablet remain connected by Bluetooth during the entire 2 hours of monitoring. The flue gas analyzer should be placed vertically and protected from dust and heat (by the cloth and umbrella).</li> <li>• While one team member is setting up the flue-gas analyzer, the second team member should be stationed near the fuel feeding zone to observe fuel feeding during the flue gas monitoring.</li> <li>• The clock on the flue gas analyzer should match the watch of the person monitoring the fuel feeding operation.</li> <li>• Once both team members are ready, flue gas monitoring begins. The team member stationed at the fuel feeding zone should record the fuel feeding status during the entire flue gas monitoring period.</li> <li>• Photograph the flue gas monitoring and fuel feeding operations, which are to be uploaded on the ODK.</li> <li>• After completion of the 2-hour monitoring, disconnect the probe, turn off the flue gas analyzer, and clean the flue gas analyzer, pipe, and tube externally.</li> <li>• After returning to the base, clean the moisture trap, check/replace the filter, and put the flue gas analyzer on the charger. Blow the flue gas probe with the bicycle pump to clean it. Periodically connect the probe and check for leaks.</li> </ul>

Table S60 – *Continued from previous page*

Day & Time	Activity
14:00 -18:00	<p>After the unloading operation for the day has been completed, count the number of bricks (row wise) for each stack and record in a table format in the notebook. Place placards on unloaded brick stacks and/or mark using lime wash. Instruct the kiln manager/unloading sardar to stack the bricks in the marked stacks or in a separate new stack the next day. Broken bricks should be collected separately in a new heap.</p> <ul style="list-style-type: none"> <li>• Before leaving the site, check the firing operation to ensure that only fuel from the weighed lot is being used. Also instruct the firing supervisor to tell all firemen and coal loaders that only fuel from the weighed lot is to be used during the night.</li> <li>• Photograph the fan, chimney, and loading chamber to be uploaded on the ODK.</li> </ul>
Day 2	
08:00 onwards	<p>One team member should observe unloading operations.</p> <ul style="list-style-type: none"> <li>• Ensure that (a) unloading only takes place from the straight region of the trench and not from the gully region; (b) unloaded bricks are being stacked in the marked stacks; and (c) almost an equal number of bricks are being unloaded from the top and bottom parts of the kiln stacking. If that is not the case, ask that the kiln manager and unloading sardar ensure that by the end of the day's unloading, an almost equal number of bricks from the top and bottom parts of the kiln stacking are unloaded.</li> <li>• Photograph of the unloading to be uploaded on the ODK.</li> </ul>
08:30 -11:30	If the flue gas analysis was not carried out on Day 1, it can be carried out during this time slot (Option 2)
09:00 onward	Completion of the 24-hour monitoring:

*Continued on next page*

Table S60 – *Continued from previous page*

Day & Time	Activity
	<ul style="list-style-type: none"> <li>• The other team member should observe the fuel feeding and talk to firemen to find out when the next chamber shifting is likely to take place. Also check the quantity of weighed fuel available, and ask that they not add excess coal to the containers before the next chamber shifting.</li> <li>• On completion of fuel measurement monitoring: Note the end time and sketch the kiln and mark the position of the fire. Also put a marker on the kiln and take a photograph. Note the number of chambers that have been completed/closed during the 24-hour monitoring.</li> <li>• Ensure that all drums that have remaining pre-weighed fuel are emptied and calculate the quantity of remaining fuel using the standard bucket measurement.</li> <li>• Check the remaining pre-weighed fuel on the tarpaulin in the fuel storage area and estimate the quantity using the standard bucket measurement.</li> <li>• Record the remaining weight of each fuel type on the ODK.</li> <li>• Record the number of chambers completed during 24 hours on the ODK.</li> <li>• Usually, the total duration of the monitoring is 24±2 hours. In some cases, if the monitoring was started on the afternoon of Day 1, the monitoring period can be reduced in order to finish monitoring during the 2 days. However, the monitoring period should not be less than 20 hours</li> </ul>
14:00-16:00	After the unloading operation for the day has been completed, count the unloaded bricks by class.

*Continued on next page*

Table S60 – *Continued from previous page*

Day & Time	Activity
	<ul style="list-style-type: none"> <li>• Count the number of bricks by rows, subtract the initial numbers, and calculate the number of bricks stacked on that day by quality class.</li> <li>• Arrange the broken bricks in a cuboid shape and measure to calculate the volume and, from that, the number of bricks (1 cubic ft = 8.5 bricks)</li> <li>• Enter the number of unloaded bricks of each quality on the ODK.</li> <li>• Randomly select and weigh 20 samples of unloaded Class 1 bricks in a lot size of 5 and enter on the ODK.</li> </ul>
16:00-17:00	<p>Check that all data have been recorded and photographs taken and that the data are correctly recorded on the ODK. Meet with the Kiln Manager/Owner, thank them for their cooperation, brief them regarding the preliminary results—e.g., specific fuel consumption, % distribution of the quantity of bricks, and interpretation of the flue gas analysis results.</p>

## References and Notes

1. M. Fowlie, R. Meeks, The Economics of Energy Efficiency in Developing Countries. *Rev. Environ. Econ. Policy* **15**, 238–260 (2021). [doi:10.1086/715606](https://doi.org/10.1086/715606)
2. IEA, Policy Pathway - Accelerating Energy Efficiency in Small and Medium-sized Enterprises 2015. (IEA Report, 2015).
3. J. Rentschler, N. Leonova, Global air pollution exposure and poverty. *Nat. Commun.* **14**, 4432 (2023). [doi:10.1038/s41467-023-39797-4](https://doi.org/10.1038/s41467-023-39797-4) [Medline](#)
4. E. Carranza, R. Meeks, Energy Efficiency and Electricity Reliability. *Rev. Econ. Stat.* **103**, 461–475 (2021). [doi:10.1162/rest\\_a\\_00912](https://doi.org/10.1162/rest_a_00912)
5. A. Iimi, R. Elahi, R. Kitchlu, P. Costolanski, Energy-Saving Effects of Progressive Pricing and Free CFL Bulb Distribution Program: Evidence from Ethiopia. *World Bank Econ. Rev.* **33**, 461–478 (2019). [doi:10.1093/wber/lhw068](https://doi.org/10.1093/wber/lhw068)
6. S. K. Pattanayak, M. Jeuland, J. J. Lewis, F. Usmani, N. Brooks, V. Bhojvaid, A. Kar, L. Lipinski, L. Morrison, O. Patange, N. Ramanathan, I. H. Rehman, R. Thadani, M. Vora, V. Ramanathan, Experimental evidence on promotion of electric and improved biomass cookstoves. *Proc. Natl. Acad. Sci. U.S.A.* **116**, 13282–13287 (2019). [doi:10.1073/pnas.1808827116](https://doi.org/10.1073/pnas.1808827116) [Medline](#)
7. N. Brooks, V. Bhojvaid, M. A. Jeuland, J. J. Lewis, O. Patange, S. K. Pattanayak, How Much do Alternative Cookstoves Reduce Biomass Fuel Use? Evidence from North India. *Resour. Energy Econ.* **43**, 153–171 (2015). [doi:10.1016/j.reseneeco.2015.12.001](https://doi.org/10.1016/j.reseneeco.2015.12.001)
8. T. Beltramo, G. Blalock, D. I. Levine, A. M. Simons, Does peer use influence adoption of efficient cookstoves? Evidence from a randomized controlled trial in Uganda. *J. Health Commun.* **20**, 55–66 (2015). [doi:10.1080/10810730.2014.994244](https://doi.org/10.1080/10810730.2014.994244) [Medline](#)
9. G. Miller, A. M. Mobarak, “Intra-household Externalities and Low Demand for a New Technology: Experimental Evidence” (NBER Working Paper No. 18964, 2013).
10. M. A. Jeuland, V. Bhojvaid, A. Kar, J. J. Lewis, O. Patange, S. K. Pattanayak, N. Ramanathan, I. H. Rehman, J. S. Tan Soo, V. Ramanathan, Preferences for improved cook stoves: Evidence from rural villages in north India. *Energy Econ.* **52**, 287–298 (2015). [doi:10.1016/j.eneco.2015.11.010](https://doi.org/10.1016/j.eneco.2015.11.010)
11. R. Hanna, E. Duflo, M. Greenstone, Up in smoke: The influence of household behavior on the long-run impact of improved cooking stoves. *Am. Econ. J. Econ. Policy* **8**, 80–114 (2016). [doi:10.1257/pol.20140008](https://doi.org/10.1257/pol.20140008)
12. N. Ryan, “Energy Productivity and Energy Demand: Experimental Evidence from Indian Manufacturing Plants” (NBER Working Paper 24619, 2018).
13. E. Somanathan, R. Somanathan, A. Sudarshan, M. Tewari, The Impact of Temperature on Productivity and Labor Supply: Evidence from Indian Manufacturing. *J. Polit. Econ.* **129**, 1667–1945 (2021). [doi:10.1086/713733](https://doi.org/10.1086/713733)
14. A. Adhvaryu, N. Kala, A. Nyshadham, “The light and the heat: Productivity co-benefits of energy-saving technology” (MIT Press Direct Working Paper 24314, 2018).

15. A. Eil, J. Li, P. Baral, E. Saikawa, “Dirty Stacks, High Stakes: An Overview of Brick Sector in South Asia” (World Bank Group Report 148140, 2020).
16. The World Bank, “Introducing Energy-efficient Clean Technologies in the Brick Sector of Bangladesh” (IBRD/World Bank Report 60155, 2011).
17. Department of Environment, National Strategy for Sustainable Brick Production in Bangladesh (2017); <https://www.ccacoalition.org/policy-database/national-strategy-sustainable-brick-production-bangladesh>.
18. GBD MAPS Working Group, “Burden of Disease Attributable to Major Air Pollution Sources in India” (Health Effects Institute Special Report 21, 2018).
19. C. Weyant, V. Athalye, S. Ragavan, U. Rajarathnam, D. Lalchandani, S. Maithel, E. Baum, T. C. Bond, Emissions from South Asian brick production. *Environ. Sci. Technol.* **48**, 6477–6483 (2014). [doi:10.1021/es500186g](https://doi.org/10.1021/es500186g) [Medline](#)
20. The World Bank, Small Study on Air Quality of Impacts of the North Dhaka Brick Cluster by Modeling of Emissions and Suggestions for Mitigation Measures including Financing Models (The World Bank report).
21. A. Jamatia, S. Chakraborti, Air Quality Assessment of Jirania Brick Industries Cluster: A Case Study. *International Journal of Scientific & Engineering Research* **6.4**, 26–28 (2015).
22. S. Ahmed, I. Hossain, Applicability of Air pollution Modeling in a Cluster of Brickfields in Bangladesh. *Chem. Eng. Res. Bull.* **12**, 28–34 (2008). [doi:10.3329/cerb.v12i0.1495](https://doi.org/10.3329/cerb.v12i0.1495)
23. S. M. M. H. Khan, M. Rana, A. K. Azad, S. Nasrin, M. Rahman, M. Asrafuzzaman, A. A. Lipi, The World Bank, Department of Environment, Sources of Air Pollution in Bangladesh (Department of Environment Report, 2019).
24. N. Brooks, D. Biswas, R. Hossin, A. Yu, S. Saha, S. Saha, S. K. Saha, S. P. Luby, Health consequences of small-scale industrial pollution: Evidence from the brick sector in Bangladesh. *World Dev.* **170**, 106318 (2023). [doi:10.1016/j.worlddev.2023.106318](https://doi.org/10.1016/j.worlddev.2023.106318)
25. A. R. Sherri, B. A. Begum, M. Baiocchi, D. Goswami, P. K. Hopke, W. A. Brooks, S. P. Luby, Associations between ambient fine particulate matter and child respiratory infection: The role of particulate matter source composition in Dhaka, Bangladesh. *Environ. Pollut.* **290**, 118073 (2021). [doi:10.1016/j.envpol.2021.118073](https://doi.org/10.1016/j.envpol.2021.118073) [Medline](#)
26. T. R. Tusher, Z. Ashraf, S. Akter, Health effects of brick kiln operations: A study on largest brick kiln cluster in Bangladesh. *South East Asia J. Public Health* **8**, 32–36 (2019). [doi:10.3329/seajph.v8i1.42270](https://doi.org/10.3329/seajph.v8i1.42270)
27. M. H. R. Khan, M. K. Rahman, A. Ajm, Y. Oki, T. Adachi, Evaluation of degradation of agricultural soils associated with brick burning in selected soil profiles in the eastern region of Bangladesh. *Nettai Nogyo* **50**, 183–189 (2006).
28. D. Biswas, E. S. Gurley, S. Rutherford, S. P. Luby, The drivers and impacts of selling topsoil for brick making in Bangladesh. *Environ. Manage.* **62**, 792–802 (2018). [doi:10.1007/s00267-018-1072-z](https://doi.org/10.1007/s00267-018-1072-z) [Medline](#)

29. A. Blackman, Informal Sector Pollution Control: What Policy Options Do We Have? *World Dev.* **28**, 2067–2082 (2000). [doi:10.1016/S0305-750X\(00\)00072-3](https://doi.org/10.1016/S0305-750X(00)00072-3)
30. A. Blackman, Alternative Pollution Control Policies in Developing Countries. *Review of Environmental Economics and Policy* **4**, 2 (2010): 234–253. <https://doi.org/10.1093/reep/req005>.
31. M. Khaliquzzaman, A. S. Harinath, S. A. Ferdousi, S. M. M. H. Khan, Thirty Years' Quest for Emission Reduction and Energy Efficiency Improvement of Brick Kilns in Bangladesh. *Int. J. Environ. Monit. Anal.* **8**, 11–22 (2020). [doi:10.11648/j.ijema.20200801.12](https://doi.org/10.11648/j.ijema.20200801.12)
32. N. Haque, Technology mandate for greening brick industry in Bangladesh: A policy evaluation. *Clean Technol. Environ. Policy* **19**, 319–326 (2016). [doi:10.1007/s10098-016-1259-z](https://doi.org/10.1007/s10098-016-1259-z)
33. S. P. Luby, D. Biswas, E. S. Gurley, I. Hossain, Why highly polluting methods are used to manufacture bricks in Bangladesh. *Energy Sustain. Dev.* **28**, 68–74 (2015). [doi:10.1016/j.esd.2015.07.003](https://doi.org/10.1016/j.esd.2015.07.003)
34. N. Brooks, D. Biswas, S. Maithel, S. Kumar, M. R. Uddin, S. Ahmed, M. Mahzab, G. Miller, M. Rahman, S. P. Luby, Building blocks of change: The energy, health, and climate co-benefits of more efficient brickmaking in Bangladesh. *Energy Res. Soc. Sci.* **117**, 103738 (2024). [doi:10.1016/j.erss.2024.103738](https://doi.org/10.1016/j.erss.2024.103738)
35. J. Lee, N. R. Brooks, F. Tajwar, M. Burke, S. Ermon, D. B. Lobell, D. Biswas, S. P. Luby, Scalable deep learning to identify brick kilns and aid regulatory capacity. *Proc. Natl. Acad. Sci. U.S.A.* **118**, e2018863118 (2021). [doi:10.1073/pnas.2018863118](https://doi.org/10.1073/pnas.2018863118) [Medline](#)
36. Department of Environment, “Registered Brick Kilns” (Government of Bangladesh DOE Report, 2023).
37. Transparency International Bangladesh, *Corruption in Service Sectors: National Household Survey 2021*. S. M. Akram and M. Haque, Eds. (Transparency International Bangladesh, 2022); pp. 1–37.
38. A. D. Foster, M. R. Rosenzweig, Microeconomics of Technology Adoption. *Annu. Rev. Econ.* **2**, 395–424 (2010). [doi:10.1146/annurev.economics.102308.124433](https://doi.org/10.1146/annurev.economics.102308.124433) [Medline](#)
39. The World Bank, “Bangladesh - Brick Kiln Efficiency Project (P105226)” (Final Implementation Status Report, 2016).
40. UNDP/GEF, “UNDP/GEF Project: Improving Kiln Efficiency in Brick Making Industry (IKEBMI) (GEF PIMS 1901)” (Terminal Evaluation Report, 2016).
41. The World Bank, “Clean Air and Sustainable Environment Project” (Implementation Completion and Results Report, 2019).
42. N. Alam, S. Barman, “Bangladesh Brick Sector Roadmap 2019-2030” (Frankfurt School Report, 2019).
43. UNDP, GEF, “Improving Kiln Efficiency in the Brick Making Industry” (UNDP PIMS #2837, Project Document, 2010)

44. Frankfurt School of Finance and Management, “Tunnel kiln technology overview and project assessment guideline” (Frankfurt School Report, 2019).
45. S. Maithel, D. Lalchandani, G. Malhotra, P. Bhanware, R. Uma, S. Ragavan, V. Athalye, K. Bindiya, S. Reddy, T. Bond, C. Weyant, “Brick kilns performance assessment” (Greentech Knowledge Solutions, 2012); <https://www.catf.us/resource/brick-kilns-performance-assessment-a-roadmap-for-cleaner-brick-production-in-india/f>.
46. S. Kumar, A. Ravi, S. Maithel, “Training Programme on cleaner fired-clay brick production practices” (Greentech Knowledge Solutions, 2016); [https://www.ccacoalition.org/sites/default/files/resources/2016\\_Training-Programme-on-Cleaner-Fired-Clay-Production-Practices\\_ICIMOD.pdf](https://www.ccacoalition.org/sites/default/files/resources/2016_Training-Programme-on-Cleaner-Fired-Clay-Production-Practices_ICIMOD.pdf).
47. S. Kumar, S. Rana, S. Maithel, Learnings from Bihar’s Experience of Implementing Cleaner Brick Kiln Directive: A Case Study (Greentech Knowledge Solutions, 2018).
48. D. Lalchandani, S. Maithel, “Towards Cleaner Brick Kilns in India” (Greentech Knowledge Solutions, 2013); <https://shaktifoundation.in/wp-content/uploads/2014/02/CATF-2013-Towards-Cleaner-Brick-Kilns-in-India.pdf>.
49. UNFCC, “Small-scale Methodology: Fuel Switch, process improvement and energy-efficiency in brick manufacture” (2015).
50. M. I. Haque, K. Nahar, M. H. Kabir, A. Salam, Particulate black carbon and gaseous emission from brick kilns in Greater Dhaka region, Bangladesh. *Air Qual. Atmos. Health* **11**, 925–935 (2018). [doi:10.1007/s11869-018-0596-y](https://doi.org/10.1007/s11869-018-0596-y)
51. R. Ahmad, Y. Zhou, C. Liang, G. Li, N. Zhao, A. Abbas, F. Yu, L. Li, J. Gong, D. Wang, Y. Yang, Z. Tang, M. Sultan, C. Sun, R. Dong, Comparative evaluation of thermal and emission performances for improved commercial coal-fired stoves in China. *RSC Adv.* **12**, 20886–20896 (2022). [doi:10.1039/D2RA03364J](https://doi.org/10.1039/D2RA03364J) [Medline](#)
52. K. Gillingham, D. Rapson, G. Wagner, The Rebound Effect and Energy Efficiency Policy. *Rev. Environ. Econ. Policy* **10**, 68–88 (2016). [doi:10.1093/reep/rev017](https://doi.org/10.1093/reep/rev017)
53. K. Rennert, F. Errickson, B. C. Prest, L. Rennels, R. G. Newell, W. Pizer, C. Kingdon, J. Wingenroth, R. Cooke, B. Parthum, D. Smith, K. Cromar, D. Diaz, F. C. Moore, U. K. Müller, R. J. Plevin, A. E. Raftery, H. Ševčíková, H. Sheets, J. H. Stock, T. Tan, M. Watson, T. E. Wong, D. Anthoff, Comprehensive evidence implies a higher social cost of CO<sub>2</sub>. *Nature* **610**, 687–692 (2022). [doi:10.1038/s41586-022-05224-9](https://doi.org/10.1038/s41586-022-05224-9) [Medline](#)
54. C. Barstow, R. Bluffstone, K. Silon, K. Linden, E. Thomas, A cost-benefit analysis of livelihood, environmental and health benefits of a large scale water filter and cookstove distribution in Rwanda. *Dev. Eng.* **4**, 100043 (2019). [doi:10.1016/j.deveng.2019.100043](https://doi.org/10.1016/j.deveng.2019.100043)
55. G. Hutton, E. Rehfuss, F. Tediosi, Evaluation of the costs and benefits of interventions to reduce indoor air pollution. *Energy Sustain. Dev.* **11**, 34–43 (2007). [doi:10.1016/S0973-0826\(08\)60408-1](https://doi.org/10.1016/S0973-0826(08)60408-1)
56. K. Gillingham, J. H. Stock, The Cost of Reducing Greenhouse Gas Emissions. *J. Econ. Perspect.* **32**, 53–72 (2018). [doi:10.1257/jep.32.4.53](https://doi.org/10.1257/jep.32.4.53)
57. K. Rennert, C. Kingdon, “Social Cost of Carbon 101” (Resources for the Future, 2022); <https://www.rff.org/publications/explainers/social-cost-carbon-101/>.



58. A. Blackman, J.-S. Shih, D. Evans, M. Batz, S. Newbold, J. Cook, The benefits and costs of informal sector pollution control: Mexican brick kilns. *Environ. Dev. Econ.* **11**, 603–627 (2006). [doi:10.1017/S1355770X06003159](https://doi.org/10.1017/S1355770X06003159)
59. A. M. Mobarak, P. Dwivedi, R. Bailis, L. Hildemann, G. Miller, Low demand for nontraditional cookstove technologies. *Proc. Natl. Acad. Sci. U.S.A.* **109**, 10815–10820 (2012). [doi:10.1073/pnas.1115571109](https://doi.org/10.1073/pnas.1115571109) [Medline](#)
60. H. Ritchie, P. Rosado, M. Roser, “CO<sub>2</sub> and Greenhouse Gas Emissions” (Our World in Data, 2023); <https://ourworldindata.org/co2-and-greenhouse-gas-emissions>
61. US EPA, “Greenhouse Gas Equivalencies Calculator” (2023); <https://www.epa.gov/energy/greenhouse-gas-equivalencies-calculator>.
62. D. Atkin, A. Chaudhry, S. Chaudry, A. K. Khandelwal, E. Verhoogen, Organizational Barriers to Technology Adoption: Evidence from Soccer-Ball Producers in Pakistan. *Q. J. Econ.* **132**, 1101–1164 (2017). [doi:10.1093/qje/qjx010](https://doi.org/10.1093/qje/qjx010)
63. G. Miller, D. Biswas, A. Mahajan, K. Babiarz, N. Brooks, J. Brunner, S. Ashraf, J. Shane, S. Maithel, S. Ahmed, M. Mazab, M. R. Uddin, M. Rahman, S. P. Luby, “A Business Case for Human Rights at Work? Experimental Evidence on Labor Trafficking and Child Labor at Brick Kilns in Bangladesh” (National Bureau of Economic Research Working Paper 32829, 2024).
64. A. Blackman, W. Harrington, The use of economic incentives in developing countries: Lessons from international experience with industrial air pollution. *J. Environ. Dev.* **9**, 5–44 (2000). [doi:10.1177/107049650000900102](https://doi.org/10.1177/107049650000900102)
65. S. Jayachandran, J. de Laat, E. F. Lambin, C. Y. Stanton, R. Audy, N. E. Thomas, Cash for carbon: A randomized trial of payments for ecosystem services to reduce deforestation. *Science* **357**, 267–273 (2017). [doi:10.1126/science.aan0568](https://doi.org/10.1126/science.aan0568) [Medline](#)
66. A. Blackman, Alternative Pollution Control Policies in Developing Countries. *Rev. Environ. Econ. Policy* **4**, 234–253 (2010). [doi:10.1093/reep/req005](https://doi.org/10.1093/reep/req005)
67. A. Blackman, G. J. Bannister, Pollution Control in the Informal Sector: The Ciudad Juárez Brickmakers’ Project. *Nat. Resour. J.* **37**, 829–856 (1997).
68. E. Somanathan, R. Bluffstone, Biogas: Clean Energy Access with Low-Cost Mitigation of Climate Change. *Environ. Resour. Econ.* **62**, 265–277 (2015). [doi:10.1007/s10640-015-9961-6](https://doi.org/10.1007/s10640-015-9961-6)
69. D. Naeher, R. Narayanan, V. Ziulu, Impacts of energy efficiency projects in developing countries: Evidence from a spatial difference-in-differences analysis in Malawi. *Energy Sustain. Dev.* **73**, 365–375 (2023). [doi:10.1016/j.esd.2023.03.010](https://doi.org/10.1016/j.esd.2023.03.010)
70. D. Atkin, D. Donaldson, I. Rasul, E. Verhoogen, C. Woodruff, S. Caria, N. Kala, A. Saggese, M. Teachout, *Firms, Trade, and Productivity* (International Growth Centre, 2021).
71. N. Bloom, A. Mahajan, D. McKenzie, J. Roberts, Why do firms in developing countries have low productivity? *Am. Econ. Rev.* **100**, 619–623 (2010). [doi:10.1257/aer.100.2.619](https://doi.org/10.1257/aer.100.2.619)
72. N. Bloom, R. Lemos, R. Sadun, D. Scur, J. Van Reenen, The New Empirics of Management. *J. Eur. Econ. Assoc.* **12**, 835–876 (2014). [doi:10.1111/jeea.12094](https://doi.org/10.1111/jeea.12094)

73. N. Bloom, C. Genakos, R. Martin, R. Sadun, Modern Management: Good for the Environment or Just Hot Air? *Econ. J.* **120**, 551–572 (2010). [doi:10.1111/j.1468-0297.2010.02351.x](https://doi.org/10.1111/j.1468-0297.2010.02351.x)
74. N. Bloom, B. Eifert, A. Mahajan, D. McKenzie, J. Roberts, Does Management Matter? Evidence from India. *Q. J. Econ.* **128**, 1–51 (2013). [doi:10.1093/qje/qjs044](https://doi.org/10.1093/qje/qjs044)
75. G. W. Imbens, J. D. Angrist, Identification and Estimation of Local Average Treatment Effects. *Econometrica* **62**, 467–475 (1994). [doi:10.2307/2951620](https://doi.org/10.2307/2951620)
76. G. W. Imbens, D. B. Rubin, Estimating Outcome Distributions for Compliers in Instrumental Variables Models. *Rev. Econ. Stud.* **64**, 555–574 (1997). [doi:10.2307/2971731](https://doi.org/10.2307/2971731)
77. N. Brooks, D. Biswas, S. Maithel, G. Miller, A. Mahajan, M. R. Uddin, S. Ahmed, M. Mazab, M. Rahman, S. P. Luby, Replication Data for: Reducing Emissions and Air Pollution from Informal Brick Kilns: Evidence from Bangladesh, Harvard Dataverse, Version 2.0 (2024); [doi:10.7910/DVN/MV9FEH](https://doi.org/10.7910/DVN/MV9FEH)
78. S. B. Bajracharya, A. Mishra, A. Hussain, K. Gurung, L. Mathema, B. Banmali Pradhan, Do working and living conditions influence brick-kiln productivity? Evidence from Nepal. *Int. J. Occup. Saf. Ergon.* **28**, 1452–1460 (2022). [doi:10.1080/10803548.2021.1899498](https://doi.org/10.1080/10803548.2021.1899498) [Medline](#)
79. P. Saha, S. Mazumder, Impact of Working Environment on Less Productivity in RMG Industries: a Study on Bangladesh RMG Sector. *GJMBR* **15**, 2 (2015).
80. K. L. Morgan, D. B. Rubin, Rerandomization to improve covariate balance in experiments. *Ann. Stat.* **40**, 1263–1282 (2012). [doi:10.1214/12-AOS1008](https://doi.org/10.1214/12-AOS1008)
81. M. Bruhn, D. McKenzie, In Pursuit of Balance: Randomization in Practice in Development Field Experiments. *Am. Econ. J. Appl. Econ.* **1**, 200–232 (2009). [doi:10.1257/app.1.4.200](https://doi.org/10.1257/app.1.4.200)
82. X. Li, P. Ding, D. B. Rubin, Asymptotic theory of rerandomization in treatment-control experiments. *Proc. Natl. Acad. Sci. U.S.A.* **115**, 9157–9162 (2018). [doi:10.1073/pnas.1808191115](https://doi.org/10.1073/pnas.1808191115) [Medline](#)
83. M. J. Uddin, P. S. Hooda, A. S. M. Mohiuddin, M. E. Haque, M. Smith, M. Waller, J. K. Biswas, Soil organic carbon dynamics in the agricultural soils of Bangladesh following more than 20 years of land use intensification. *J. Environ. Manage.* **305**, 114427 (2022). [doi:10.1016/j.jenvman.2021.114427](https://doi.org/10.1016/j.jenvman.2021.114427) [Medline](#)
84. International Labour Organization (ILO), *Small-Scale Brickmaking* (ILO, Technical memorandum No. 6, 1984).
85. J. Angrist, J.-S. Pischke, *Mostly Harmless Econometrics: An Empiricist's Companion* (Princeton Univ. Press, 2009); pp. 1–84.